

7-8-2021

Spinning Behaviour of Egyptian Cotton/Waste Blends on Open End Spinning System.

S. Ibrahim

Assistant Professor, Textile Engineering Department, Faculty of Engineering, Mansoura University, Mansoura, Egypt.

Rizk El-Beally

Assistant Professor, Textile Engineering Department, Faculty of Engineering, Mansoura University, Mansoura, Egypt.

Follow this and additional works at: <https://mej.researchcommons.org/home>

Recommended Citation

Ibrahim, S. and El-Beally, Rizk (2021) "Spinning Behaviour of Egyptian Cotton/Waste Blends on Open End Spinning System.," *Mansoura Engineering Journal*: Vol. 5 : Iss. 1 , Article 12.

Available at: <https://doi.org/10.21608/bfemu.2021.182653>

This Original Study is brought to you for free and open access by Mansoura Engineering Journal. It has been accepted for inclusion in Mansoura Engineering Journal by an authorized editor of Mansoura Engineering Journal. For more information, please contact mej@mans.edu.eg.

SPINNING BEHAVIOUR OF EGYPTIAN COTTON/WASTE
BLENDS ON OPEN END SPINNING SYSTEM

BY

* **
S. Ibrahim and R. El-Beally

Long and medium cotton wastes, either individually or blended with lower grades of cotton were blended to produce open-end yarns. The effect of blending ratios of the waste on the properties of produced yarn have been examined. Different blowing rooms, single and tandem card, one and two drawing passages were used to process the slivers for open-end yarns. In addition BD 200 R_c and platt sacelowell open-end spinning machines were used.

It was found that the waste of long staple egyptian cotton, containing considerable amount of good fibres is suitable for open-end processing. Blended wastes of long fibres with lower grade raw cotton slightly decrease the quality of open end yarn. Tandem card is more suitable for sliver preparation of open-end yarns produced from waste.

1. INTRODUCTION:

Since the first open end spinning machine was introduced in 1965, a huge number of studies were performed to investigate the properties of this new type of yarn. Many of these studies dealt making comparison between open end yarn and ring spun yarn properties. Another group of investigations was done to study the internal structure of open end yarn. A further group of researches trials to dealt with the study of optimum conditions either mechanically or technologically for producing economically high quality open end yarn. Some of these studies showed the effect of raw material properties open end yarn. Because of the nature informed, it is agreed to some extent use finer fibres for producing it.

* Lecturer) Textile Engineering
** Ass. Teacher) Eng. El-Mansoura U.
EGYPT.
Mansoura Bulletin v

(2) and
used. Th
Given in Tar
type

The minimum number of fibres in the cross-section of open end yarn is greater than that in ring spun yarns. Since the formation of open-end yarn requires higher twist than that for ring spun yarn, shorter fibres are of significant importance.

Recently, few works have been published on the possibility of producing open end yarn using cotton waste. The Egyptian cotton waste containing remarkably high portion of good fibres is suitable for processing open end yarns. The paradox of processing cotton waste by open end spinning system arises when one knows that:

- i) The slivers for open end spinning must be very clean.
- ii) The waste contains trashes, fragments of fibres and micro-dust, these types of trashes become a source of troubles for open end spinning.

The present work deals mainly with two problems; firstly the effect of blending ratio of cotton waste blended with raw cotton, and secondly the effect of machine aggregation on sliver preparation, namely the type of blowing room and carding machine. All yarns were produced under industrial conditions to reflect a real picture for the possibility of producing high quality of open end yarn using Egyptian cotton waste.

2. MATERIAL AND FIBRE MEASUREMENTS:

2.1. Material Used:

Raw cottons (Giza 66, Giza 67 and Giza 69); cotton waste" flat strips, comber noil and card slivers" which was extracted from long staple Egyptian cottons "Giza 68 and Giza 70" were selected to achieve a homogeneous blend as possible. Both raw cotton and cotton wastes were blended with different ratios and spun to open end yarn of different counts.

Given in Table (1) the characteristics of the various types of raw cottons used in the experiments. Given in Tables (2) and (3) the main properties of waste and cotton/waste blend. The percent ratio of waste to raw cotton properties is given in Table (4).

Table (1): Properties of Medium and Long Staples
Egyptian Cottons

Fibre Property	Type of cotton					
	Giza 66	Dendara	Giza 67	Giza 69	Giza 68	Giza70
<u>Fibre Length:</u>						
Effective Length(mm)	32.6	33.50	34.56	33.84	34.30	36.0
Mean length (mm)	24.3	24.05	26.30	25.82	27.60	27.2
C.V %	33.8	36.0	28.30	33.29	32.30	30.2
Short fibre % < ½"	11.7	15.20	10.20	9.34	11.0	10.8
<u>Fibre Fineness:</u>						
µg/inch	4.24	3.61	4.36	3.98	3.55	4.13
<u>Fibre Strength:</u>						
Pressely index	8.63	8.70	9.90	9.77	10.13	11.10

Table (2): Properties of cotton wastes Extracted From
Egyptian cottons.

Type of cotton wastes	Fibre property					
	Micronaire reading µg/inch	Pressley index	Effective length (mm)	Mean length mm	Short fibre %	C.V %
<u>For Giza 68</u>						
Comber noil	3.26	8.51	33.40	22	25.0	48.7
flat strips	3.60	9.20	33.60	25	20.2	47.6
<u>For Giza 70</u>						
Comber noil	3.60	9.80	32.10	22	21.0	45.21
flat strips	4.04	9.96	35.0	24	13.0	45.60
<u>For Giza 67</u>						
Card slivers	4.30	9.60	30.0	24	10.1	35.30

Table (3): Fibre properties in Blends.

Type of Blend	Blending Ratios				Fibre Property		
	raw cotton	Comber noil	waste flat strips	card card sliver	Micronaire reading $\mu\text{g}/\text{inch}$	Pressely index	Mean length (mm)
Giza66/waste*	75	12.5	8.5	4	4.13	8.91	23.99
	50	25.0	17	8	3.99	9.53	23.00
Giza66/noil of Giza 66	75	25.0	-	-	3.94	8.10	24.61
	50	50.0	-	-	3.74	8.80	21.80
Giza66/strips of Giza 68	75	-	25	-	4.20	9.17	25.37
	50	-	50	-	4.00	8.15	24.27
Giza67/noil of Giza 68	50	50.0	-	-	3.80	9.95	24.00
Giza69/noil of Giza 70	75	25.0	-	-	4.00	9.80	24.80

* waste (noil and strips from Giza 70 + card sliver from Giza 67).

Table (4): Waste properties Relative to Mean Fibre properties.

Type of waste	Fibre property					
	micronaire reading $\mu\text{g}/\text{inch}$	pressly index	effective length (mm)	mean length (mm)	short fibre %	C.V%
Comber noil	0.858	0.865	0.932	0.804	2.11	1.51
Card strips	0.952	0.903	0.975	0.894	1.52	1.49
Card sliver	0.986	0.969	0.868	0.910	0.99	1.25

2.2. Fibre Measurements:

The main properties of individual components and blends were measured according to A.S.T.M.

- Fibre length distribution was determined using the sutter webb tester.

- Fibre strength measurements were carried out using pressly flat bundle strength tester at zero gauge, and,
- Fibre fineness in terms of $\mu\text{g}/\text{inch}$ using shiffeld micronaire tester.

3. YARN PRODUCTION AND MEASUREMENTS:

3.1. Method:

Different types of yarns were produced to investigate the effect of both blending ratio and machine aggregation on open end yarn quality. The specifications of open end yarns produced are given in Table (5).

Table (5)

Type of Blend	Giza66/waste blend			Giza67/waste blend			Giza69/waste blend		
Blend ratio	100 _C	75 _C	50 _C	100 _W	100 _C	50 _C	100 _W	100 _C	75 _C
		25 _W	50 _W			50 _W			25 _W
Yarn count	The count produced was mostly Ne 14 and T/inch = 16								

The following systems were used for producing open-end yarn with different preparations:

Group I: Trützschler Blow Room/Tandem Card or single card/first or and second drawing frames/Open-end spinning machine "BD 200 Rc".

The material used for this group is Giza 67/noil blends, the yarn were processed at Dakahilia spinning mill.

Group II: Hergith Blow Room/Single card/first or and second Drawing frame/either BD200Rc or platt open end spinning machine.

The materials used for this group are Giza 66/noil, Giza 66/strips and Giza 69/noil blends. The yarns were processed at El-Mahalla spinning and weaving company.

3.2. Machine Specification:

1) Blowing Room: The blends were processed through:

- 1- Trützschler Line: Blending Bale opener-Automatic Hopper feeder-Step cleaner-Fine cleaner-Fine Opener and Scutcher Lap m/c.

2- Hergeith Blowing Room: Blending Bale opener-Automixer-Vertical opener-Step cleaner-porcupine beater-Hopper Feeder Two bladed beater - Kirschner beater.

ii) Carding Machines: The material was fed in the form of a lap through single or tandem card machine:

1- Single card (Tyoda). The laps were carded and N_m 0.253 (3.94 g/m) card sliver was produced at cylinder speed of 200 r.p.m.

2- Tandem card: A card Sliver was produced at cylinder speed of 300 r.p.m. and Taker-in speed was 800 r.p.m.

iii) Drawing Frame: The card sliver was processed into N_m 0.253 (3.949/m). First and second drawing sliver on ZINSEK drawing frame Model 720, Using 8 doubling and 8 draft.

iv) Open-End Spinning Frame:

1- BD 200 Rc open-end machine with rotor speed of 36000 r.p.m. and combing roller speed of 6000 r.p.m.

2- Platt sacco-Lowell machine, with rotor speed of 40000 r.p.m. and opening roller speed of 5000 r.p.m.

3.3. Yarn Measurements:

All yarns produced on open-end spinning machines from raw cotton, cotton wastes and cotton/waste blends were examined for:-

- Yarn count and count variation by uster Autosorter.
- Yarn strength in grams, percentage extension at break and strength variability, uster tensomatt tester was used and 200 tests per yarn was performed.
- The evenness of slivers, yarns were measured by uster Evenness tester, at the sametime, yarn imperfections have been measured "neps, thin and thick places/1000 meter".

4. RESULTS AND DISCUSSIONS:

4.1. Material Selection:

The main fibre properties of the card sliver wastes indicated in Table (4) compared with comber noil and card flat strips are found to be close to the properties of raw cotton.

Table (1) and (2), show that the waste which was extracted from long staple cottons has a slight lower quality than that of the raw cottons used and close to that of medium raw cottons. In general the waste and its blend have properties sufficient to produce coarser open end yarns of good quality.

4.2. Effect of Blending Ratio on open-End Yarn Properties:

(i) Yarn Strength:

It has been found previously that the open end yarns has low tenacity than that of ring spun yarns processed from the same cotton. The observed low strength of open end yarns can be attributed to poor fibre extent /1/.

Table (6) and graph (1) show the effect of blending ratio on the strength of open end yarns produced from different cotton/waste blends. It was found that when both raw cotton and wastes were blended, the strength of yarn has been slightly decreased as the proportion of cotton wastes in the blend increased. The tenacity of open end yarns produced from 100% cotton wastes and cotton/waste blends are fairly close to each other.

(ii) Yarn Extension:

The elongation of open-end yarns is usually reported to be higher than that of ring spun yarn/3/. However the conditions operating during open end spinning can affect this property. In some cases a similar elongation to that found in ring spun yarns is reported.

In the present work it was found that yarn extension for various 100% cotton is slightly higher than for 100% waste except for 100% cotton (G67) and 100% noil of G 70.

Douglas /5/ in his work found for open end yarn of 12.5^S (50 tex), with twist factor 5.5 that the extension is ranging between 9.8 to 10.7%, which is considered high for the length of fibre used (from 9 to 12 mm) in comparison with that obtained for yarns produced for longer fibres (22 to 27 mm) in the present work.

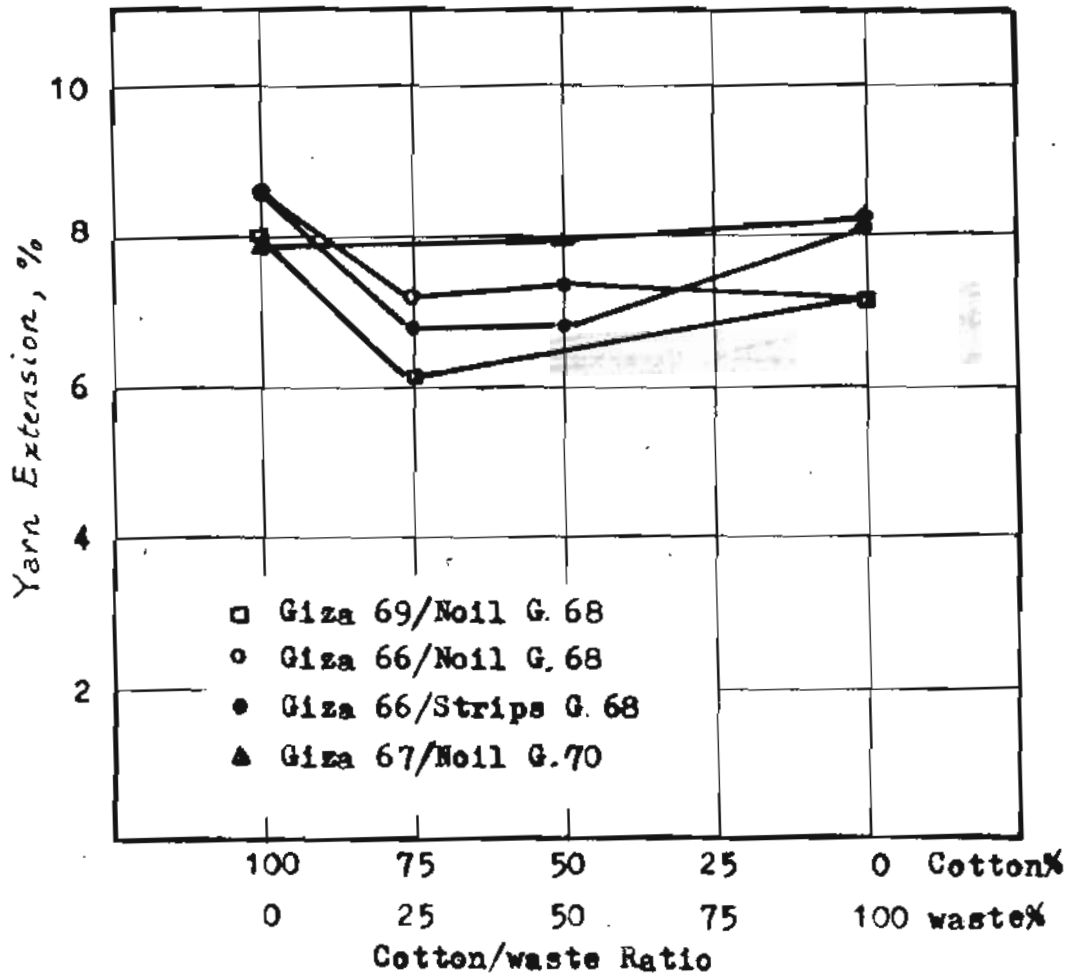


Fig. 2. Relationship between Yarn Extension and Cotton/waste Ratio

iii) Yarn Irregularity:

The distribution of fibre length and the linear density of fibres are very important factors affecting the irregularity of yarn. As expected increasing the percentage of short fibres due to blending with wastes increases irregularity.

Fig.(3) show that yarn irregularity C.V% increases as the percentage of waste increases for all types of fibres. Also, the coefficient of variation values for the yarn produced from 100% noils or its blend are higher than those produced from flat strips. Table (9) shows the imperfection (neps, thin and thick places/1000 m). Generally as the percent of waste increases imperfections increases. Main imperfection is nep, where the probability of nep formation increases due to the existance of higher percentage of dead and half mature fibres in the blend compared with that in the raw cotton used.

4.3. The Effect of Machine Aggregation on Open End Yarn Properties

(i) Yarn Strength:

Yarn strength and type of carding machine: Table (8) shows the results obtained by processing 100% raw cotton of various types either on single card or tandem card. The tenacity of yarns which were processed on tandem card have higher values than those processed on single card. This may be interpreted with reference / 4/, which stated that: "The unmatched degree of fibre individualisation achieved by tandem card leads to improved drafting, facilitates trash extraction by the open-end trash eliminator and provide a smoother flow of fibres into the spinning rotor. In fact these factors contribute to improve yarn strength.

Yarn strength and Number of Drawing passages:

From Table (8) and Fig.(4), It could be concluded that for the same material the tenacity increases using double drawing passages, this due to more straighten and parallization of fibres. The results obtained indicate that yarns produced on BD 200 Rc machine have higher strength than that produced on platt open-end machine. And that both yarn have almost the same evenness, Also the ends down/1000 spindls hrs is less for platt O.E machine than that obtained on BD 200 for the same procedure of material preparation.

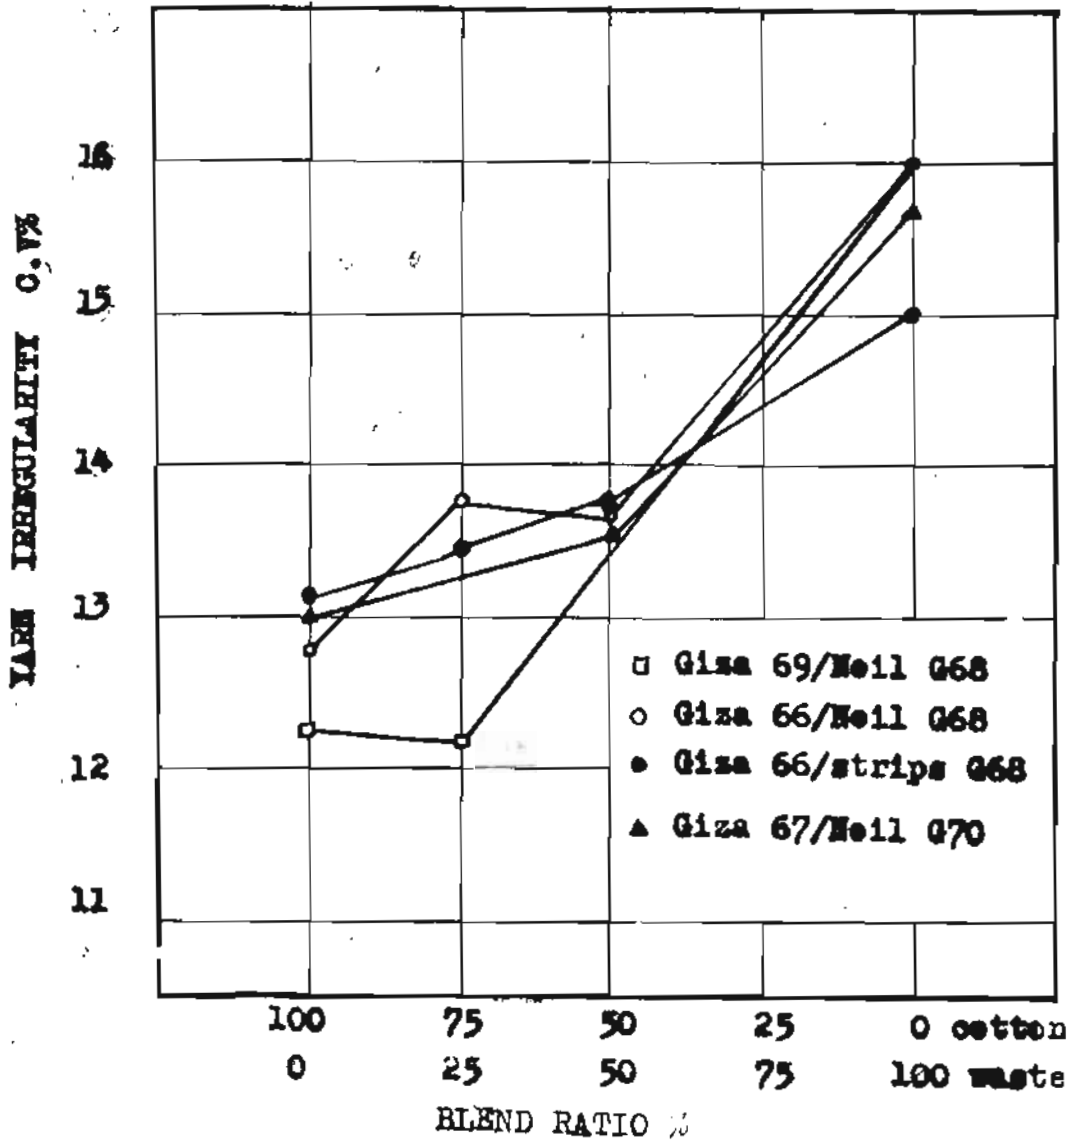


Fig.(3) The Effect of Blending Ratio On open-end Yarn Irregularity

TABLE (7) Properties of Open end Yarns spun from Cotton/waste blends produced on SD₂CC and Platt C.D Spinning M/C.

Cotton - End Spinning M/C	BD 200 No M/C.				Platt Saco-Lowell M/C.					
	Giza 66/strips		Giza 66/Noil		Giza 66/strips		Giza 66/Noil			
Blend	50c	75c	100c	50c	50c	75c	100c	75c	50c	
	50W	25W		25W	50W	50W	25W	100c	25W	50W
Measures Count "Ne"	13.69	14.09	14.08	13.87	13.77	14.18	14.09	13.67	13.63	14.0
Measured T.P.I	16.10	15.95	16.85	15.75	16.17	15.65	16.60	16.95	17.55	15.82
Single end Strength (C)	524.89	508.7	534.25	536.08	518.85	466.87	466.0	495	456.6	486.8
% elongation	6.8	6.80	8.5	7.20	7.36	5.38	5.3	5.9	5.7	5.3
Yarn Tenacity (C/tex)	12.17	12.14	12.55	12.54	12.10	11.26	11.12	11.5	10.54	11.64
Break Factor (C B.P)	958	1050	867	981	991	907	930	934	831	928
Lea strength C.V%	1.12	6.3	5.31	6.54	7.71	3.44	3.47	3.82	7.15	1.96
Yarn Irregularity C.V%	13.69	13.44	12.79	13.75	14	13.53	13.88	12.88	13.63	13.21
Spins down /1000 unit Hrs	219	250	15.6	107	15.0	74	40	21	21	29

Noil and Strips were extracted from Giza 66 cotton
 Noil yarn count Ne 14 with T.P.I : 16

TABLE (8) Effect of Preparation Systems On Open-end
Yarn Characteristics

Material	Giza 67/Noil (G.70) blend								
	Blend % 100c		50c/50w		100w				
	Tandem card system	F/S	single card	F	Tandem card	F/S			
Yarn Count	12	12	12	14	24	14	14	14	14
Measured count	11.7	12	12.7	13.51	23.63	14.5	25.1	14.5	13.8
Measured T.P.I	14.3	14.5	14.5	17.47	24.2	15.42	23.2	16.3	15.7
Single end Strength (G)	598	541.2	502	457.8	257	501.5	241	447	502
C.V% of yarn Strength	12.2	8.9	9.2	11.1	11.0	5.91	12.9	15.7	11.0
% elongation	7.5	7.1	6.6	8.12	8.27	7.51	6.34	8.45	8.3
Yarn Tenacity (G/tex)	11.84	11.0	10.79	10.90	10.28	12.32	10.24	10.56	10.6
Yarn Irregularity C.V%	13.2	11.8	13.40	13.69	15.0	12.24	13.45	16.7	15.6

F : First Drawing passage

F/S: First and second Drawing passages.

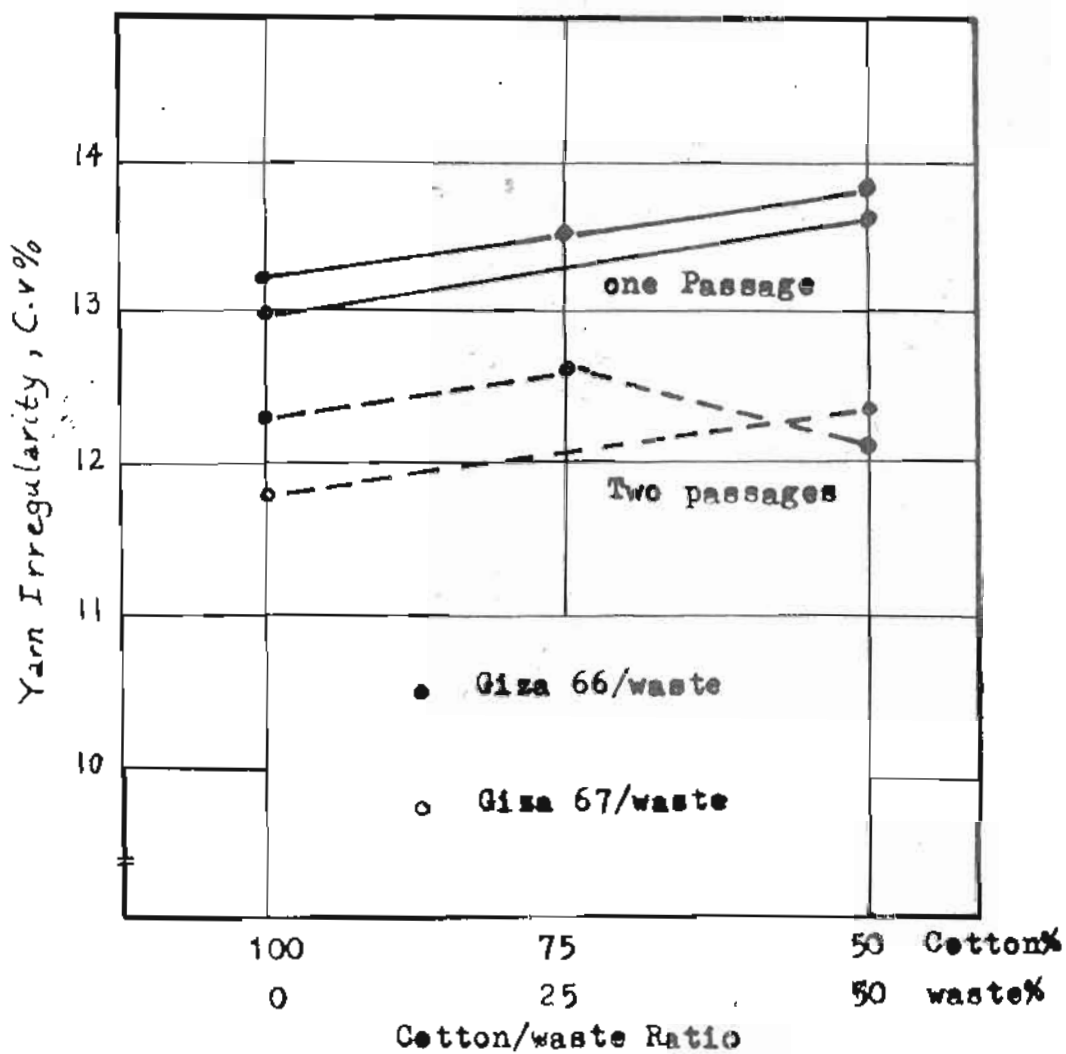


Fig. 4. Effect of Number of Drawing Passages on Open-End Yarn Irregularity

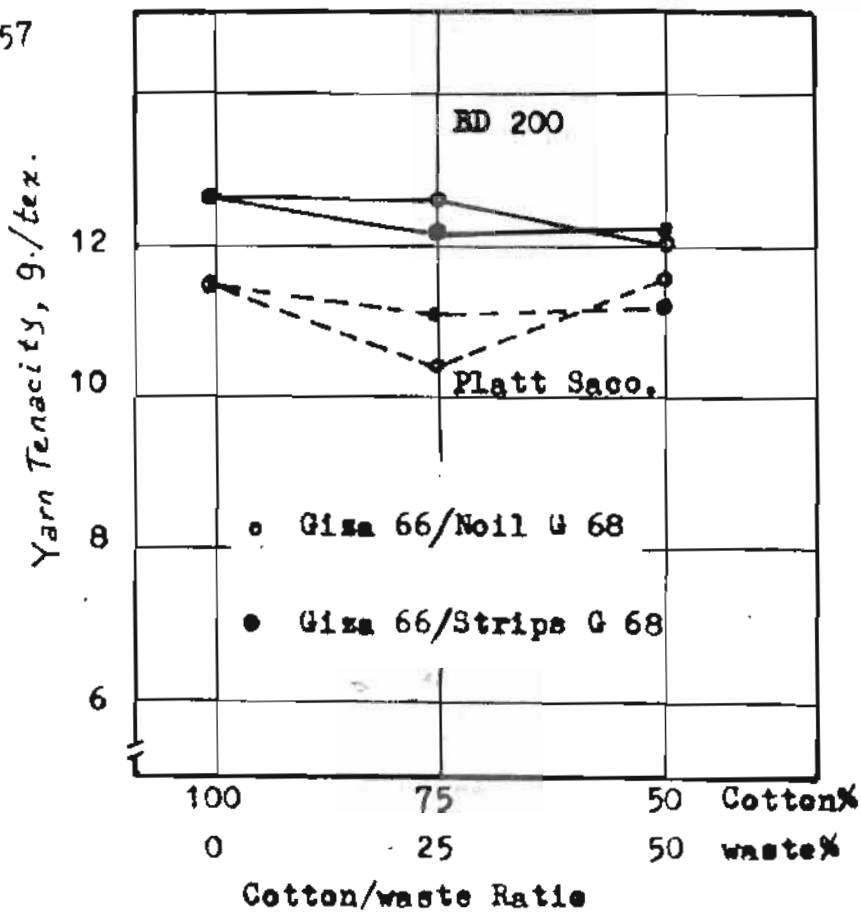


Fig. 5 . Influence of Machine Type on Yarn Tenacity

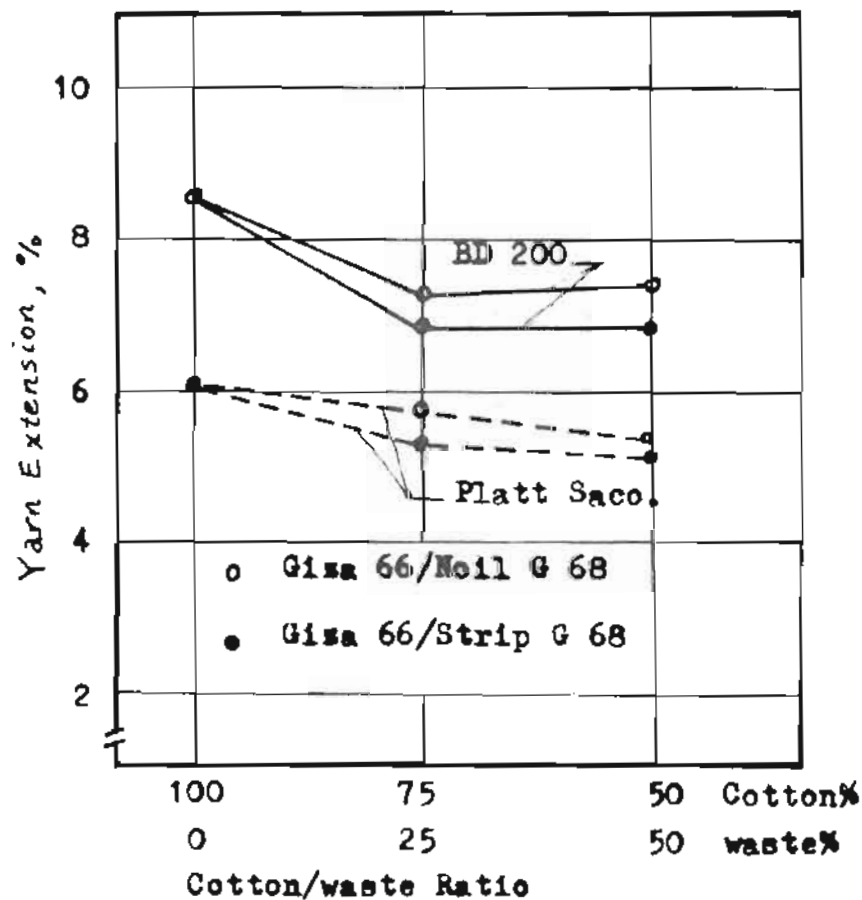


Fig. 6 . Influence of Machine Type on Yarn Extension

Table (9)- Effect of Blends and Preparation System
on the Irregularity of Open-End Yarns

Preparation System	Yarn Irregularity C. V. %	Giza 66/waste blend				Giza 67/waste blend		
		100C	75C 25w	50C 50w	100w	100C	50C 50w	100w
Tandem Card	C.V%	13.2	13.55	13.81	14.52	13.2	13.69	16
with First	Thin Places	15	17	24	7	4	4	16
Drawing	Thick Places	42	34	32	26	13	16	41
Passage	Neps	346	263	358	375	24	66	234
Tandem Card	C.V%	12.3	12.63	12.04	12.6	11.79	12.3	13.6
with First &	Thin Places	4.0	5.0	1.0	7.0	1	1	6
Second	Thick Places	9.0	9.0	11	11	5	10	17
Drawing	Neps	114	110	110	170	22	59	60
Passage								
Single Card	C.V%	14				13.4		
	Thin Places	12				7		
	Thick Places	20				11		
	Neps	112				47		

(ii) Yarn Irregularity:

Yarn Irregularity and type of carding machine:

Table (9) shows the effect of using tandem or single card on yarn irregularity, No significant differences in the yarn irregularity due to the use of tandem card in comparison to the use of single card.

Yarn Irregularity and the number of Drawing passages:

From Table (9) and graph (4), it could be seen that, the irregularity of the yarn processed using tandem card and double drawing passages are lower than using only one drawing passages. Also, the number of imperfections per 1000 meters are reduced. In general this is contrary to what is known in drafting theory, where the increase of short fibres produce more trouble during drafting processes. The number of doubling (2 x 8 times) used in drawing, the use of Autoleveler, the excellent cyclic doubling/6/ of fibres inside the rotor seems to have equalled the negative effect of short fibres and led to the reduction of the influence of short fibres on yarn irregularity.

5. CONCLUSIONS:

- i) The waste of long staple Egyptian cotton contain high percentage of spinnable fibres, suitable for producing acceptable quality open end yarn.
- ii) In the case of blends of raw cotton and waste, as the percentage of waste increases the tenacity slightly decreases.
- iii) The extension of open end yarn produced from a blend of raw cotton and noil, is higher than those produced from blends of raw cotton and strips.
- iv) As the percentage of waste increases in the blend the irregularity increases.
- v) The quality of yarns processed through spinning lines including tandem card was found to be higher than that processed through lines including single card.

- vi) For blends contains wastes of short fibres, cyclic doubling of fibres inside the rotor improved yarn irregularity which has been resulted from drawing.

REFERENCES:

1. Locher - Kaspark, "Open-end yarn analysis" Textile Industries, 9(1967).
2. F.Bancroft and C.A. Lawrence, "Progress in Open-end Spinning Shirley Institute publications S.16 page 37.
3. Sultan and El-Hwary, "Comparison of the properties of Open-end and ring spun yarns produced from two Egyptian cotton" J. Tex. Inst. 4(1974).
4. P.M. Grafion "Cotton sliver preparation for spinning system". Rotor spinning Technical and Economic Aspects By Dyson. Page. 23
5. K. Douglas "Processing of waste fibres by means of rotor spinning" Zelliueger uster Ltd. uster suwtzerland, "Rotor spinning technical and economic aspects", edited by E.Dyson Textile trade press P. 203.
6. Krause - Soliman: Textile Res. J. 41, No. 2 Feb. 1971.