

6-15-2021

## Effect of Solar Cell Surface Coating on Conversion Efficiency.

Mahmoud Kandil

*Head of Electrical Power Engineering Department, Faculty of Engineering, Mansoura University, Mansoura, Egypt.*

Mohamed Tantawy

*Assistant Professor, Electrical Power & Machines Department, Faculty of Engineering, Mansoura University, Mansoura, Egypt., mtantawi@mans.edu.eg*

Mofreh Mofreh

*Computer & systems Engineering Department, Faculty of Engineering, Mansoura University, Mansoura, Egypt.*

Follow this and additional works at: <https://mej.researchcommons.org/home>

---

### Recommended Citation

Kandil, Mahmoud; Tantawy, Mohamed; and Mofreh, Mofreh (2021) "Effect of Solar Cell Surface Coating on Conversion Efficiency.," *Mansoura Engineering Journal*: Vol. 5 : Iss. 1 , Article 15.

Available at: <https://doi.org/10.21608/bfemu.2021.184370>

This Original Study is brought to you for free and open access by Mansoura Engineering Journal. It has been accepted for inclusion in Mansoura Engineering Journal by an authorized editor of Mansoura Engineering Journal. For more information, please contact [mej@mans.edu.eg](mailto:mej@mans.edu.eg).

EFFECT OF SOLAR CELL SURFACE COATING  
ON  
CONVERSION EFFICIENCY  
=====

BY

\* M. S. KANDIL, \*\* M. A. TANTAWY & \*\*\* MOPREH MOHAMED

ABSTRACT :

The paper illustrates the use of antireflecting layers for coating solar cell surface in order to improve the conversion efficiency. These coatings may be in single or multilayer. Mathematical analysis are given to determine the reflection losses in both cases .

Through numerical application, by the use of computer programming, and regarding the economical point of view a comparison is made between the conversion efficiency for solar cells with and without antireflection coatings.

INTRODUCTION :

To improve the conversion efficiency of solar cells, the different conversion losses must be reduced as much as possible. Coating the solar cell surface with materials having intermediate reflection coefficient between the air and the solar cell material has considerable effect on the reduction of reflection losses. Also the multiplication of antireflection layers the conversion efficiency .

The materials used for single-layer cell surface coating usually are  $MgF_2$  ,  $SiO_2$  ,  $Al_2O_3$  ,  $SiO$  and  $CeO_2$  ( Ref. 2 9 ) . Acomparicon between these materials is illustrated through the numerical application given later. With respect to couble- layer antireflection coatings, the first layer can be made from  $MgF_2$  or  $LiF$  of  $SiO_2$  and the second layer is usually made from  $TiO_2$  with thickness 0.045 microns. For triple - layer antireflection coating, the first layer materials are usu/ or  $SiO_2$  , the second layer is made from  $ZrSiO_4$  , wit microns and the third layer is usually ma thickness 0.048 microns .

5/1/80

\* Head of Electrical Power & Machines Engineering, El-Mansoura University

\*\* Assistant Prof., Faculty of Engine University .

\*\*\* Assistant Lecturer, Faculty of E University .

Vol., 5, No . 1 , June 1980 .

MATHEMATICAL FORMULATION :

The reflection loss using a multi-layer antireflection coatings ( Ref. 3 ) is given by :

$$R = \left| \frac{a}{b} \right|^2 \dots\dots\dots ( 1 )$$

where :

$$\begin{bmatrix} a \\ b \end{bmatrix} = \begin{bmatrix} N_0 & -1 \\ N_0 & 1 \end{bmatrix} \cdot \begin{bmatrix} \cos \delta_k & j \frac{\sin \delta_k}{N_k} \\ j N_k \cdot \sin \delta_k & \cos \delta_k \end{bmatrix} \cdot \begin{bmatrix} 1 \\ N_s \end{bmatrix} \dots\dots\dots ( 2 )$$

and  $\delta_k = \frac{2\pi}{\lambda} N_k \cdot t_k \dots\dots\dots ( 3 )$

where :

- $N_0$  is the refractive index of the air,
- $N_k$  is the refractive index of the K th coating layer,
- $N_s$  is the refractive index of the solar cell material,
- $t_k$  is the thickness of the K th coating layer
- &  $\lambda$  is the wave length of the incident light.

1- Single - layer Antireflection coating :

Coating the solar cell with a single - layer antireflection coating of material , whose refractive index,  $N_1$  , and thickness,  $t_1$ . The phase difference introduced by two consecutive reflection,  $\delta_1$ , on cell with refractive index,  $N_2$  . The reflection loss can be obtained from eqs ( 1,2,3 ) as

$$\begin{bmatrix} a \\ b \end{bmatrix} = \begin{bmatrix} N_0 & -1 \\ N_0 & 1 \end{bmatrix} \cdot \begin{bmatrix} \cos \delta_1 & j \frac{\sin \delta_1}{N_1} \\ j N_1 \cdot \sin \delta_1 & \cos \delta_1 \end{bmatrix} \cdot \begin{bmatrix} 1 \\ N_2 \end{bmatrix}$$

where :

$$\delta_1 = \frac{2\pi}{\lambda} N_1 \cdot t_1 \dots\dots\dots ( 4 )$$

Therefore,

$$\begin{bmatrix} a \\ b \end{bmatrix} = \begin{bmatrix} (N_0 - N_2) \cdot \cos \delta_1 + j \left( \frac{N_0 N_2}{N_1} - N_1 \right) \cdot \sin \delta_1 \\ (N_0 + N_2) \cdot \cos \delta_1 + j \left( \frac{N_0 N_2}{N_1} + N_1 \right) \cdot \sin \delta_1 \end{bmatrix} \dots (5)$$

If :  $A = (N_0 - N_2) \cdot \cos \delta_1$  , ..... (6 a)

$B = \left( \frac{N_0 N_2}{N_1} + N_1 \right) \cdot \sin \delta_1$  , ..... (6 b)

$C = (N_0 + N_2) \cdot \cos \delta_1$  ..... (6 c)

&

$D = \left( \frac{N_0 N_2}{N_1} - N_1 \right) \cdot \sin \delta_1$  ..... (6 d)

so,

$$\begin{bmatrix} a \\ b \end{bmatrix} = \begin{bmatrix} A + jB \\ C + jD \end{bmatrix} \dots (7)$$

and from eq ( 1,7 ), the reflection loss for a single-layer antireflection coating is

$$R = \frac{A^2 + B^2}{C^2 + D^2} \dots (8)$$

2-Double - layer Antireflection Coating :

This system consists of two layer, the first layer is met by the air , whose refractive index,  $N_1$ , and thickness,  $t_1$ , the second layer is attached to the solar cell surface, whose refractive index,  $N_2$ , and thickness,  $t_2$ , the refractive index of the solar cell is  $N_3$ . The reflection loss expression for double-layer antireflection coatings can be obtained from eq ( 1,2,3 ) as

$$\begin{bmatrix} a \\ b \end{bmatrix} = \begin{bmatrix} N_0 & -1 \\ N_0 & 1 \end{bmatrix} \cdot \begin{bmatrix} \cos \delta_1 & j \frac{\sin \delta_1}{N_1} \\ j N_1 \cdot \sin \delta_1 & \cos \delta_1 \end{bmatrix} \cdot \begin{bmatrix} \cos \delta_2 & j \frac{\sin \delta_2}{N_2} \\ j N_2 \cdot \sin \delta_2 & \cos \delta_2 \end{bmatrix} \cdot \begin{bmatrix} 1 \\ N_3 \end{bmatrix}$$

where :

$$\delta_1 = \frac{2\pi}{\lambda} N_1 \cdot t_1 \quad \dots (9a)$$

and

$$\delta_2 = \frac{2\pi}{\lambda} N_2 \cdot t_2 \quad \dots (9b)$$

$$\begin{aligned} \left[ \begin{array}{l} a \\ b \end{array} \right] &= \left[ \begin{array}{l} \left[ (N_0 - N_3) \cdot \cos \delta_1 \cdot \cos \delta_2 + \left( \frac{N_1 \cdot N_3}{N_2} - \frac{N_0 \cdot N_2}{N_1} \right) \cdot \sin \delta_1 \cdot \sin \delta_2 \right] \\ + j \left[ \left( \frac{N_0 \cdot N_3}{N_2} - N_2 \right) \cdot \cos \delta_1 \cdot \sin \delta_2 \right. \\ \left. + \left( \frac{N_0 \cdot N_3}{N_1} - N_1 \right) \cdot \sin \delta_1 \cdot \cos \delta_2 \right] \\ \left[ (N_0 + N_3) \cdot \cos \delta_1 \cdot \cos \delta_2 - \left( \frac{N_1 \cdot N_3}{N_2} + \frac{N_0 \cdot N_2}{N_1} \right) \cdot \sin \delta_1 \cdot \sin \delta_2 \right] \\ + j \left[ \left( \frac{N_0 \cdot N_3}{N_2} + N_2 \right) \cdot \cos \delta_1 \cdot \sin \delta_2 \right. \\ \left. + \left( \frac{N_0 \cdot N_3}{N_1} + N_1 \right) \cdot \sin \delta_1 \cdot \cos \delta_2 \right] \end{array} \right] \\ &\dots (10) \end{aligned}$$

If :

$$A = N_0 - N_3, \quad B = \frac{N_1 \cdot N_3}{N_2} - \frac{N_0 \cdot N_2}{N_1},$$

$$C = \frac{N_0 \cdot N_3}{N_2} - N_2, \quad D = \frac{N_0 \cdot N_2}{N_1} - N_1,$$

$$E = N_0 + N_3, \quad F = \frac{N_1 \cdot N_3}{N_2} + \frac{N_0 \cdot N_2}{N_1},$$

$$G = \frac{N_0 \cdot N_3}{N_2} + N_2, \quad H = \frac{N_0 \cdot N_2}{N_1} + N_1,$$

$$\begin{aligned}
 I &= \cos \delta_1 \cdot \cos \delta_2 & , J &= \sin \delta_1 \cdot \sin \delta_2 & , \\
 K &= \cos \delta_1 \cdot \sin \delta_2 & \& L &= \sin \delta_1 \cdot \cos \delta_2 & .
 \end{aligned}$$

So, the reflection loss for a double - layer antireflection coating is :

$$R = \frac{(A.I + B.J)^2 + (C.K + D.L)^2}{(E.I - F.J)^2 + (G.K + H.L)^2} \dots\dots\dots (11)$$

3- Triple - layer Antireflection Coating :

This system consists of three layers. The first layer is met by the air, whose refractive index,  $N_1$ , and thickness,  $t_1$ . The second is medium between the first and the third, whose refractive index,  $N_2$ , and thickness,  $t_2$ . The third is attached to the solar cell surface, whose refractive index,  $N_3$ , and thickness,  $t_3$ .

If :

$N_0$  is the refractive index of the air

&

$N_4$  is the refractive index of the solar cell .

So, the reflection loss expression for triple - layer antireflection coatings can be obtained as

$$\begin{bmatrix} a \\ b \end{bmatrix} = \begin{bmatrix} N_0 & -1 \\ N_0 & 1 \end{bmatrix} \begin{bmatrix} \cos \delta_1 & j \frac{\sin \delta_1}{N_1} \\ jN_1 \cdot \sin \delta_1 & \cos \delta_1 \end{bmatrix} \begin{bmatrix} \cos \delta_2 & j \frac{\sin \delta_2}{N_2} \\ jN_2 \cdot \sin \delta_2 & \cos \delta_2 \end{bmatrix} \begin{bmatrix} \cos \delta_3 & j \frac{\sin \delta_3}{N_3} \\ jN_3 \cdot \sin \delta_3 & \cos \delta_3 \end{bmatrix} \begin{bmatrix} 1 \\ N_4 \end{bmatrix}$$

Where :  $\delta_1 = \frac{2\pi}{\lambda} N_1 \cdot t_1 \dots\dots\dots (12 a)$

$\delta_2 = \frac{2\pi}{\lambda} N_2 \cdot t_2 \dots\dots\dots (12 b)$

$\delta_3 = \frac{2\pi}{\lambda} N_3 \cdot t_3 \dots\dots\dots (12 c)$

If :

$$A = N_0 - N_4 \quad , \quad B = \frac{N_2 N_4}{N_3} - \frac{N_0 N_3}{N_2} \quad ,$$

$$C = \frac{N_1 N_4}{N_3} - \frac{N_0 N_3}{N_1}, \quad D = \frac{N_1 N_4}{N_2} - \frac{N_0 N_2}{N_1}$$

$$E = \frac{N_0 N_4}{N_3} - N_3, \quad F = \frac{N_0 N_4}{N_2} - N_2$$

$$G = \frac{N_0 N_4}{N_1} - N_1, \quad H = \frac{N_1 N_3}{N_2} - \frac{N_0 N_2 N_4}{N_1 N_3}$$

$$I = N_0 + N_4, \quad J = \frac{N_2 N_4}{N_3} + \frac{N_0 N_3}{N_2}$$

$$K = \frac{N_1 N_4}{N_3} + \frac{N_0 N_3}{N_1}, \quad L = \frac{N_1 N_4}{N_2} + \frac{N_0 N_2}{N_1}$$

$$M = \frac{N_0 N_4}{N_3} + N_3, \quad N = \frac{N_0 N_4}{N_2} + N_2$$

$$O = \frac{N_0 N_4}{N_1} + N_1, \quad P = \frac{N_1 N_3}{N_2} + \frac{N_0 N_2 N_4}{N_1 N_3}$$

$$Q = \cos \delta_1 \cdot \cos \delta_2 \cdot \cos \delta_3, \quad ,$$

$$S = \cos \delta_1 \cdot \sin \delta_2 \cdot \sin \delta_3, \quad ,$$

$$T = \sin \delta_1 \cdot \cos \delta_2 \cdot \sin \delta_3, \quad ,$$

$$U = \sin \delta_1 \cdot \sin \delta_2 \cdot \cos \delta_3, \quad ,$$

$$V = \cos \delta_1 \cdot \cos \delta_2 \cdot \sin \delta_3, \quad ,$$

$$W = \cos \delta_1 \cdot \sin \delta_2 \cdot \cos \delta_3, \quad ,$$

$$Y = \sin \delta_1 \cdot \cos \delta_2 \cdot \cos \delta_3, \quad ,$$

$$Z = \sin \delta_1 \cdot \sin \delta_2 \cdot \sin \delta_3$$

$$\begin{aligned}
a = & \left[ \left( \frac{N_0 - N_4}{N_3} \right) \cdot \cos \delta_1 \cdot \cos \delta_2 \cdot \cos \delta_3 \right. \\
& + \left( \frac{N_2 N_4}{N_3} - \frac{N_0 N_3}{N_2} \right) \cdot \cos \delta_1 \cdot \sin \delta_2 \cdot \sin \delta_3 \\
& + \left( \frac{N_1 N_4}{N_3} - \frac{N_0 N_3}{N_1} \right) \cdot \sin \delta_1 \cdot \cos \delta_2 \cdot \sin \delta_3 \\
& \left. + \left( \frac{N_1 N_4}{N_3} - \frac{N_0 N_2}{N_1} \right) \cdot \sin \delta_1 \cdot \sin \delta_2 \cdot \cos \delta_3 \right] \\
& + j \left[ \left( \frac{N_0 N_4}{N_3} - N_3 \right) \cdot \cos \delta_1 \cdot \cos \delta_2 \cdot \sin \delta_3 \right. \\
& + \left( \frac{N_0 N_4}{N_2} - N_2 \right) \cdot \cos \delta_1 \cdot \sin \delta_2 \cdot \cos \delta_3 \\
& + \left( \frac{N_0 N_4}{N_1} - N_1 \right) \cdot \sin \delta_1 \cdot \cos \delta_2 \cdot \cos \delta_3 \\
& \left. + \left( \frac{N_1 N_3}{N_2} - \frac{N_0 N_2 N_4}{N_1 N_3} \right) \cdot \sin \delta_1 \cdot \sin \delta_2 \cdot \sin \delta_3 \right] \dots (13a)
\end{aligned}$$

and

$$\begin{aligned}
b = & \left[ \left( N_0 + N_4 \right) \cdot \cos \delta_1 \cdot \cos \delta_2 \cdot \cos \delta_3 \right. \\
& - \left( \frac{N_2 N_4}{N_3} + \frac{N_0 N_3}{N_2} \right) \cdot \cos \delta_1 \cdot \sin \delta_2 \cdot \sin \delta_3 \\
& - \left( \frac{N_1 N_4}{N_3} + \frac{N_0 N_3}{N_1} \right) \cdot \sin \delta_1 \cdot \cos \delta_2 \cdot \sin \delta_3 \\
& \left. - \left( \frac{N_1 N_4}{N_2} + \frac{N_0 N_2}{N_1} \right) \cdot \sin \delta_1 \cdot \sin \delta_2 \cdot \cos \delta_3 \right] \\
& + j \left[ \left( \frac{N_0 N_4}{N_3} + N_3 \right) \cdot \cos \delta_1 \cdot \cos \delta_2 \cdot \sin \delta_3 \right. \\
& + \left( \frac{N_0 N_4}{N_2} + N_2 \right) \cdot \cos \delta_1 \cdot \sin \delta_2 \cdot \cos \delta_3 \\
& + \left( \frac{N_0 N_4}{N_1} + N_1 \right) \cdot \sin \delta_1 \cdot \cos \delta_2 \cdot \cos \delta_3 \\
& \left. - \left( \frac{N_1 N_3}{N_2} + \frac{N_0 N_2 N_4}{N_1 N_3} \right) \cdot \sin \delta_1 \cdot \sin \delta_2 \cdot \sin \delta_3 \right] \dots (13b)
\end{aligned}$$

So, the reflection loss for a triple-layer antireflection coating is

$$R = \frac{(A.Q + B.S + C.T + D.U)^2}{(I.Q - J.S - K.T - L.U)^2} + \frac{(E.V + F.W + G.Y + H.Z)^2}{(M.V + N.W + O.Y - P.Z)^2} \quad (14)$$

NUMERICAL APPLICATION AND RESULTS :

To illustrate the effect of cell surface coating with multi-layers, a Silicon solar cell is considered, and the reflection losses is computed for different materials usually used for layers surface coating .

Figs. ( 1,2,3,4 and 5 ) shows the reflection losses against wave-length for the silicon solar cell coated by a single-layer made of  $MgF_2$  or  $SiO_2$  or  $Al_2O_3$  or  $SiO$  or  $CeO_2$ .

Fig s. ( 6,7 and 8 ) illustrate the reflection loss as function of wave-length for the different layer materials used and with different layer thickness .

Fig s. ( 9 and 10 ) show the reflection losses in case of triple layer antireflection coatings.

Table ( 1 ) gives the minimum values for antireflection losses with the multi-layer antireflection coating. Also, Fig. ( 11 ) illustrates the comparison between these cases.

CONCLUSION :

To improve the solar cell conversion efficiency the reflection loss may be reduced by the use of multi-layer antireflection coatings . From the above analysis and applications, the effects of multi-layer antireflection coatings for silicon solar cell can be summerized as :

- 1 - Coating the cell with  $SiO_2$  as single - layer, the reflection loss is reduced from 31 % to 18.2 % .
- 2 - Coating the cell with  $MgF_2 - TiO_2$  as double - layer, the reflection loss will be 5.3 % .
- 3 - Coating the cell with  $MgF_2 - ZrSiO_4 - TiO_2$  , as triple - layer, the reflection loss is 2.4 % .

So, for increasing the cell conversion efficiency and regarding economical considerations, it is recommended to use  $MgF_2 - ZrSiO_4 - TiO_2$  as triple - layer antireflection coating to reduce the reflection loss from 31 % to 2.4 % .

REFERENCES:

- 1 -"Limitations and possibilities for improvement of photovoltaic solar energy converters ", M. WOLF, Proc. IRE , P.1246, July 1960 .
- 2 -" Interspecimen comparison of the refractive index of fused silica ", I.H.MALITSON, J. Opt. Soc. Amer., V.55, No. 10, P.1205 , 1965 .

E. 66. Kandil et al

- 3 - A. NUSSBAUN and R. A. PHILLIPS, " Contemporary optic for scientists and engineers ", Prentice-Hall, New - York , 1976 .
- 4 - " Solar cells ", CHARLES E. BACKUS, IEEE PRESS , New - York, 1976 .
- 5 - I. M. BLAIR, B.D. JONES and A.J. VAN HORN, " Aspects of energy conversion ", Pergamon Press, Oxford, 1976 .
- 6 - " International Conference on Solar Energy ", Nice-FRANCE, January, 1977 .
- 7 - RICHARD C. NEVILLE, " The Solar cell ", Elsevier Comp. , New - York, 1978 .
- 8 - MOFREH M. SALEM, " Possibilities for efficiency improvement of solar cells;" M. Sc. thesis, El-Mansoura University, 1979 .

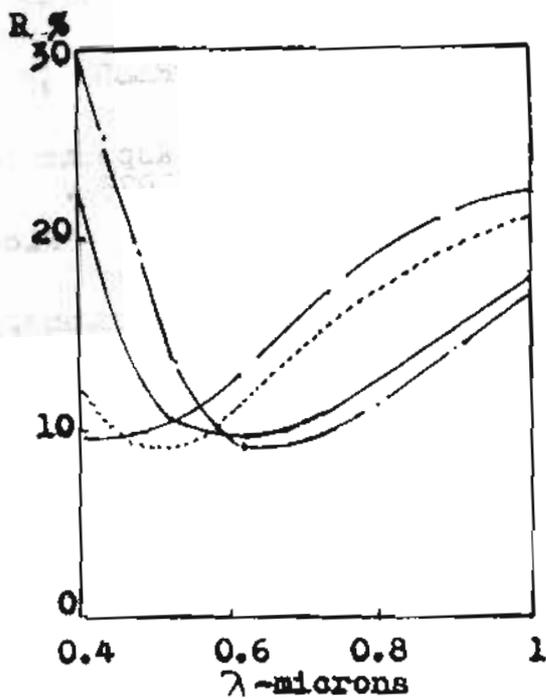


Fig (1):  $MgF_2/Si-Si$

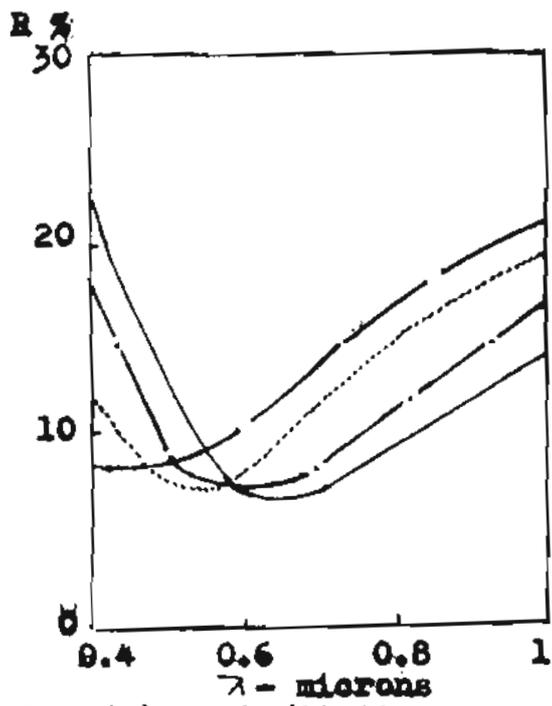


Fig (2):  $SiO_2/Si-Si$

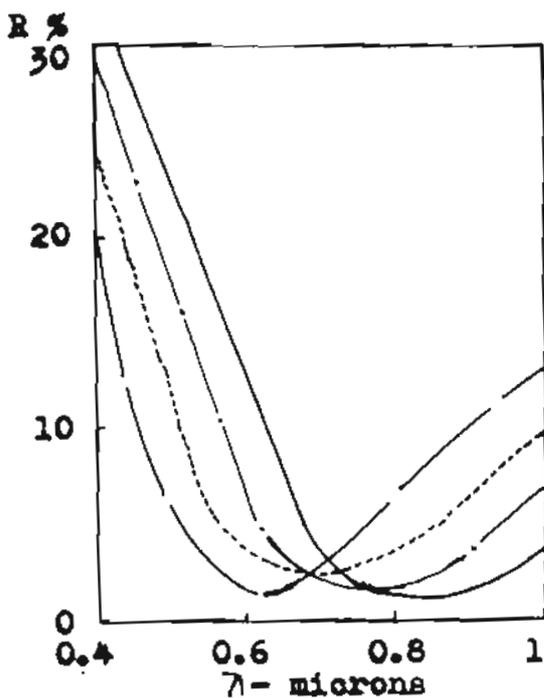


Fig (3):  $Al_2O_3/Si-Si$

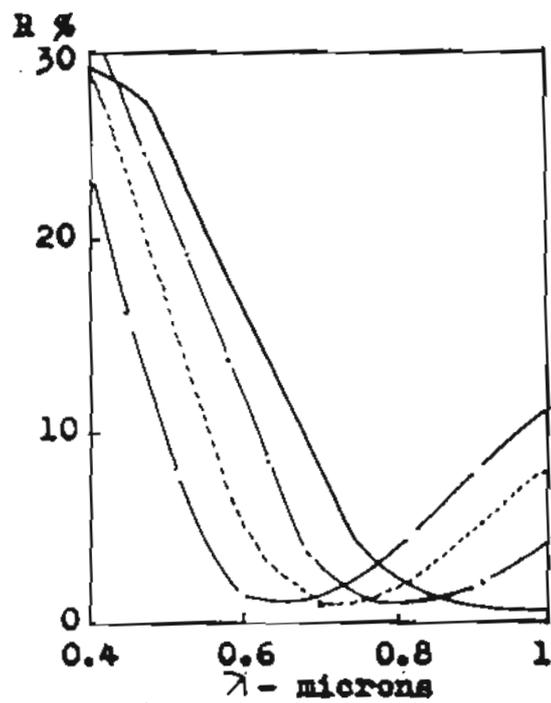


Fig (4):  $SiO/Si-Si$

—————  $t_1 = 0.08$  microns  
 - - - - -  $t_1 = 0.10$

.....  $t_1 = 0.09$   
 ————  $t_1 = 0.11$

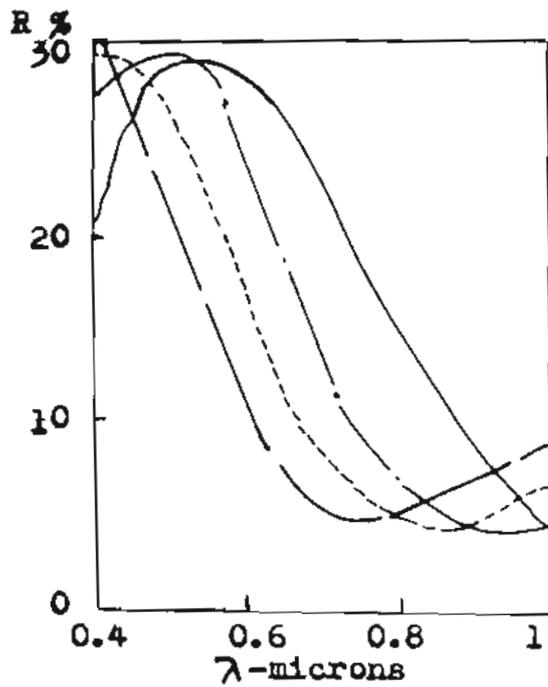


Fig (5):  $\text{CeO}_2 / \text{Si-Si}$

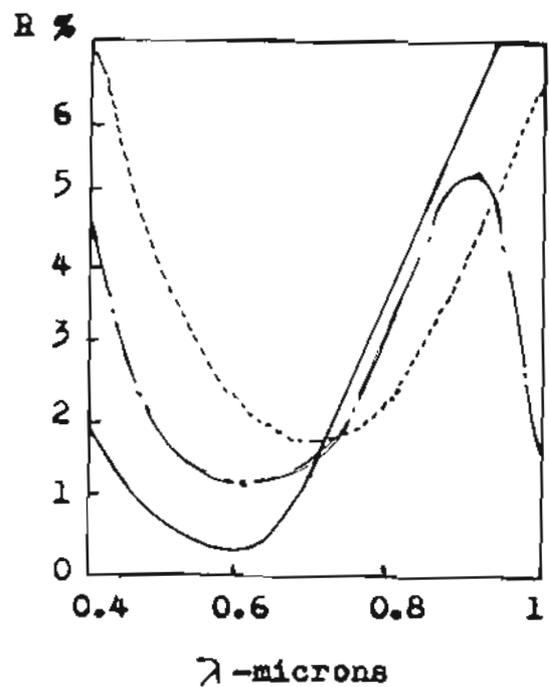


Fig (6):  $\text{MgF}_2\text{-TiO}_2 / \text{Si-Si}$

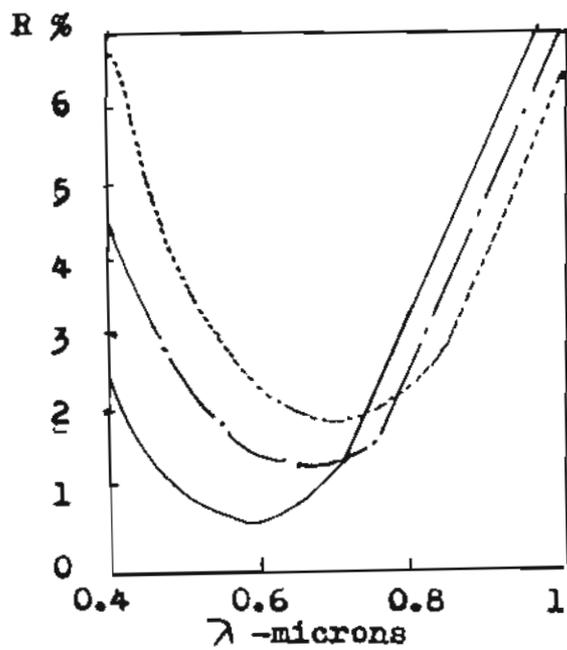


Fig (7):  $\text{LiF-TiO}_2 / \text{Si-Si}$

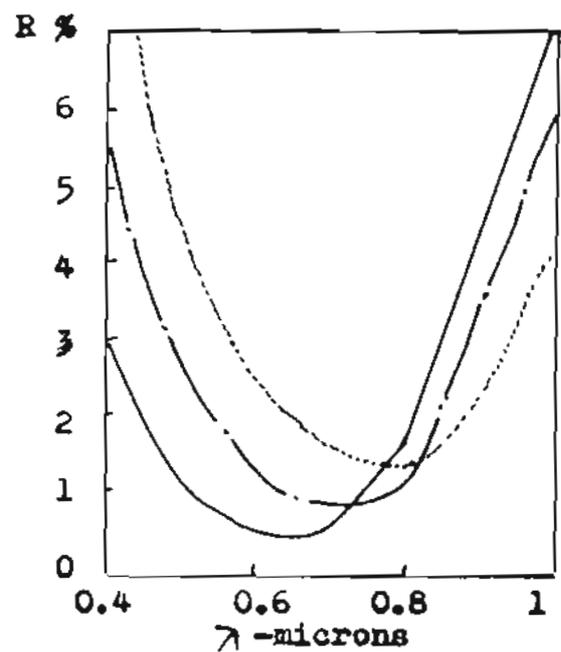


Fig (8):  $\text{SiO}_2\text{-TiO}_2 / \text{Si-Si}$

Fig (5) :	—	$t_1 = 0.08$	— · — · —	$t_1 = 0.09$
	- - -	$t_1 = 0.10$	—	$t_1 = 0.11$
Fig (6,7,8)	—	$t_1 = 0.10$	— · — · —	$t_1 = 0.11$
	- - -	$t_1 = 0.12$		

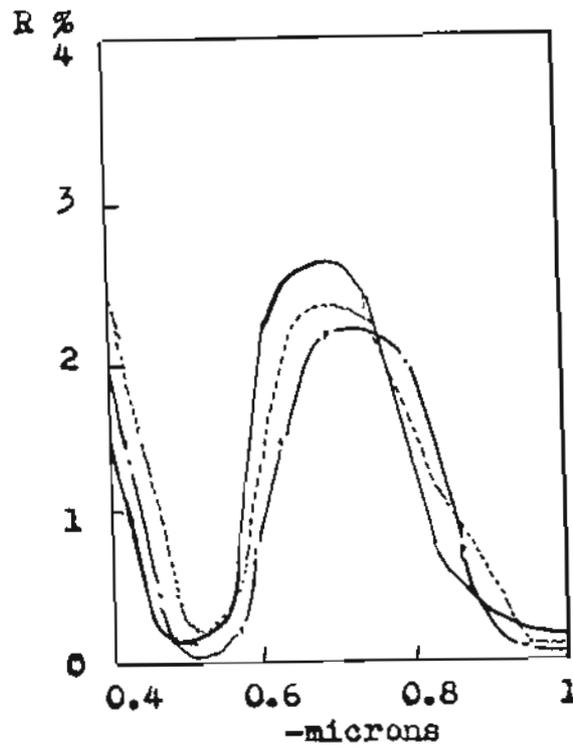


Fig (9):  $\text{MgF}_2 - \text{Zr SiO}_4 - \text{TiO}_2 / \text{Si} - \text{Si}$

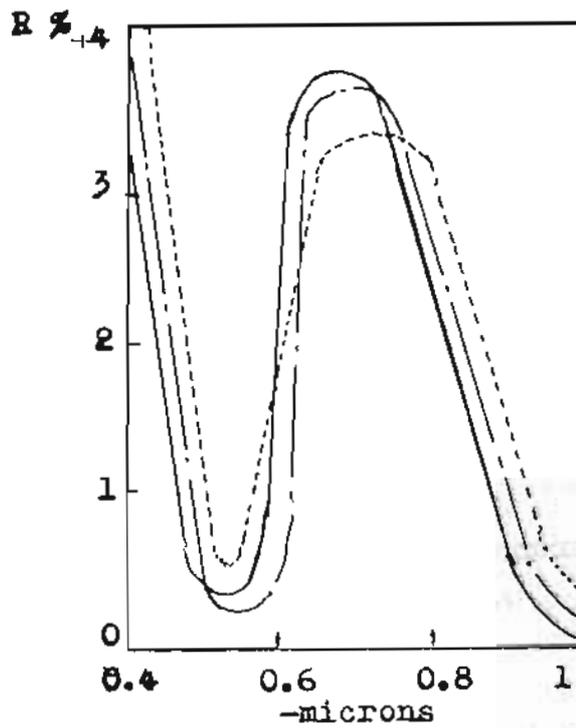


Fig (10):  $\text{SiO}_2 - \text{Zr SiO}_4 - \text{TiO}_2 / \text{Si} - \text{Si}$

—————  $t_1 = 0.85$

.....  $t_1 = 0.95$

—————  $t_1 = 0.90$

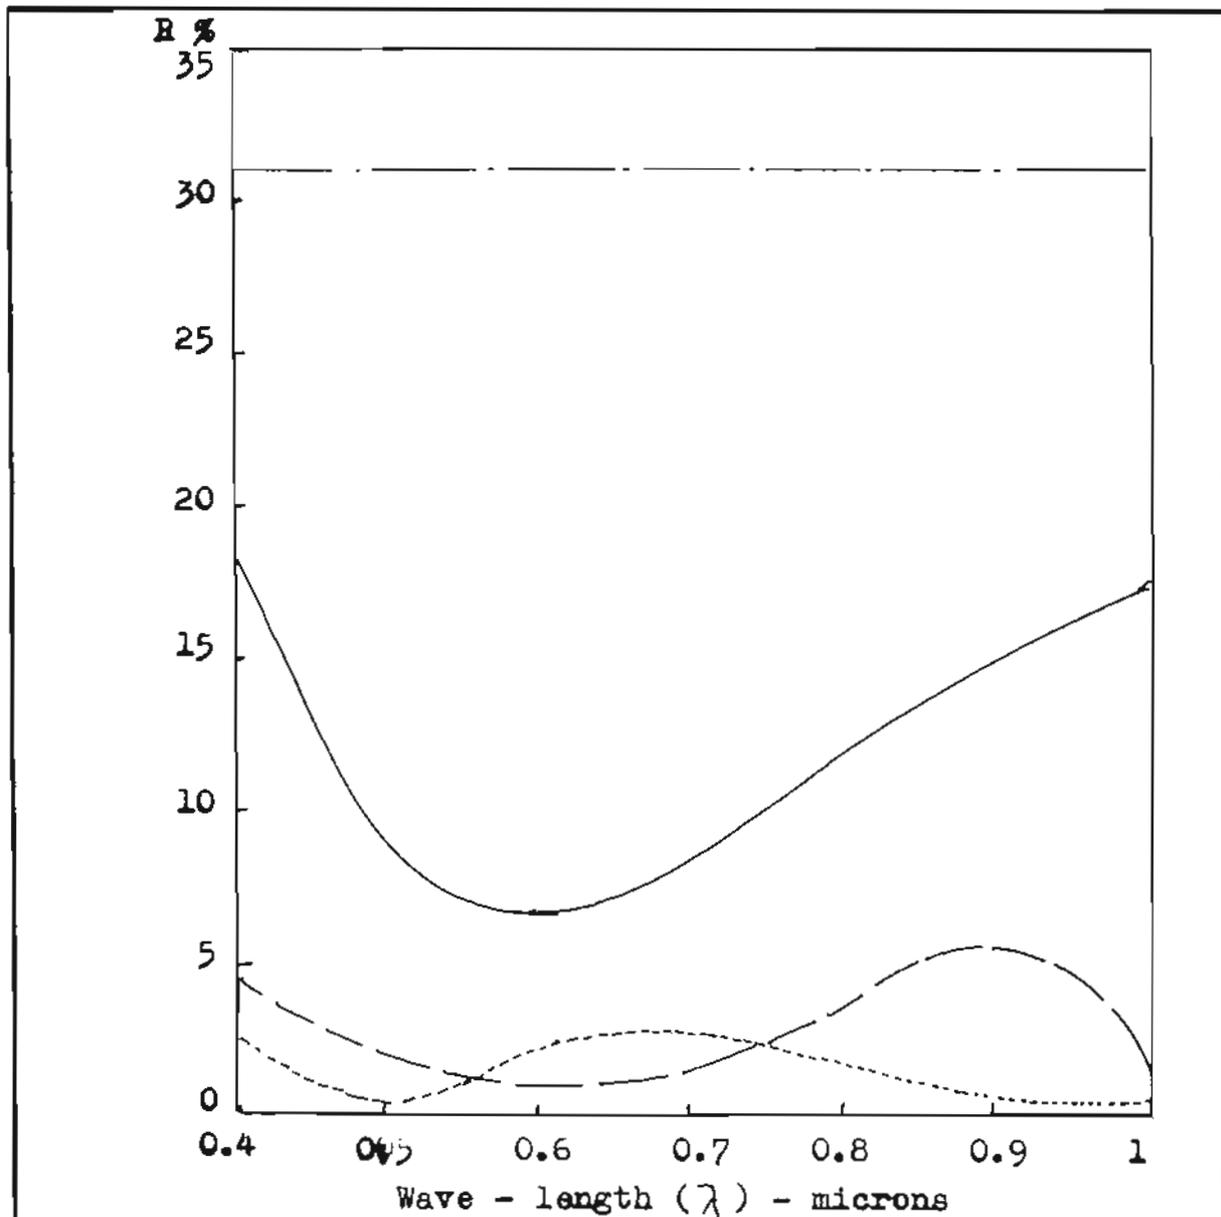


Fig (11): The reflection loss as a function of the wave - length for a different cases of antireflection coatings .

- Uncoated
- Single - layer (  $\text{SiO}_2$  )
- - - Double - layer (  $\text{MgF}_2\text{-TiO}_2$  )
- ..... Triple - layer (  $\text{MgF}_2\text{-ZrSiO}_4\text{-TiO}_2$  )

Table (1) : The reflection loss values for multi-layer antireflection coating on silicon solar cell .

anti-reflection coatings	Materials			Layer thickness ( microns )			reflection loss %
	first layer	second layer	third layer	first layer	second layer	third layer	
uncoated	-	-	-	-	-	-	31
single-layer	SiO <sub>2</sub>	-	-	0.10	-	-	18.2
double-layer	MgF <sub>2</sub>	TiO <sub>2</sub>	-	0.11	0.045	-	5.3
triple-layer	MgF <sub>2</sub>	ZrSiO <sub>4</sub>	TiO <sub>2</sub>	0.09	0.066	0.048	2.4