

5-29-2021

Effect of Weave Angle on the Geometrical Properties of Square Plain Fabrics of Circular and Elliptical Thread Cross Sections.

Hemdan Abou-Taleb

Assistant Professor., Textile Engineering Department., Faculty of Engineering., El-Mansoura University., Mansoura., Egypt., haboutaleb@mans.edu.eg

Ahmed El Deeb

Assistant Professor., Textile Engineering Department., Faculty of Engineering., El-Mansoura University., Mansoura., Egypt., asamy@mans.edu.eg

Follow this and additional works at: <https://mej.researchcommons.org/home>

Recommended Citation

Abou-Taleb, Hemdan and El Deeb, Ahmed (2021) "Effect of Weave Angle on the Geometrical Properties of Square Plain Fabrics of Circular and Elliptical Thread Cross Sections.," *Mansoura Engineering Journal*: Vol. 13 : Iss. 2 , Article 21.

Available at: <https://doi.org/10.21608/bfemu.2021.173276>

This Original Study is brought to you for free and open access by Mansoura Engineering Journal. It has been accepted for inclusion in Mansoura Engineering Journal by an authorized editor of Mansoura Engineering Journal. For more information, please contact mej@mans.edu.eg.

EFFECT OF WEAVE ANGLE ON THE GEOMETRICAL PROPERTIES
OF SQUARE PLAIN FABRICS OF CIRCULAR AND
ELLIPTICAL THREAD CROSS SECTIONS

تأثير زاوية النسيج على الخواص الهندسية للمنسوجات المربعة
المتزنة ذات الخيوط الدائرية والمقطع ناقص المقتطع
By

A.S.M. EL-DEEB AND H.A. ABO-TALEB

Textile Engineering Dept., Faculty of Engineering, Mansoura University,
Mansoura, EGYPT

خلاصة - تم اقتراح نموذج رياضي لتركييب نسجي مربعة متزن يمكن فيه انضغاط مساحة مقطع الخيوط المنسوجة الى شكل القطع الناقص مع ثبات طول محط المقطع ، وبعد تحديد الحد الاقصى لزاوية النسيج تحت عدة قيم مختلفة من معامل التعرطح والعلاقة الرياضية التي تربط بين زاوية النسيج وزاوية الالتفاف يمكن التوصل الى العلاقات الرياضية التي تربط بين بعض الخواص الهندسية لهذا التركيب النسجي وهي معامل التفتية ، نسبة التشريب والورن النسبي مع زاوية النسيج عند درجات مختلفة من التعرطح .

ABSTRACT - A general theoretical approach is presented for a geometrical model of square plain woven fabric, allowing the threads to be compressed to an elliptical cross section provided that their circumference is constant. The limitation of the assumed model i.e. jamming condition represented by weave angle was computed and the relation between wrap angle and weave angle was also obtained for different values of flattening factor. Mathematical relations between cover factor, crimp percentage, relative fabric weight and weave angle were then possible to be computed at different values of flattening factor.

1. NOMENCLATURE

- d : Thread diameter.
p : Thread spacing.
 θ : Weave angle, i.e. maximum angle of the thread axis to plane of cloth, degrees.
K : Thread cover factor.
 K_c : Fabric cover factor.
C : Crimp percentage.
L : Length of thread axis between planes containing the axes of consecutive cross threads (crimped length).
W : Fabric weight, gm / M².
n : Number of threads per cm.
T : Thread count, tex.
r : Thread radius.
a & b : Semi-major and semi-minor axes of the elliptical thread cross-section.
e : Flattening factor (b/a).
 $P_c \& P_e$: Perimeters of circular and elliptical thread cross section respectively.
 $A_c \& A_e$: Areas of circular and elliptical thread cross section respectively.
 β : (90 - wrap angle), degrees.
h : Maximum displacement of the thread axis, normal to the plane of the cloth.
D : Sum of the two diameters of warp and weft threads.

In the succeeding paragraphs the subscripts 1,2 represent the warp and weft directions respectively.

2. INTRODUCTION

The problem of fabric geometry has been the subject of study by a number of workers [1-4]. Who have studied mainly plain fabric of circular or race-track thread cross sections.

When threads are wound onto a package or woven into a fabric the ends and picks will exert pressure on each other at intersections points and the threads tend to flatten each other. Woven fabrics may also be exposed to external flattening forces during end use or ironing. Low-twist threads flatten very easily, but as the twist increases it becomes progressively more difficult to distort its cross-section under pressure [5].

Thread flattening during and after fabric formation has a great influence on some fabric properties such as cover, crimp, weight, thickness and maximum thread setting, which may affect in turn on fabric thermal conductivity, air permeability, crease-resistance, stiffness, appearance, handle, shrinkage, tensile properties and abrasion resistance.

As most of the world's textiles are woven fabric and most of that woven fabric are mainly nearly square plain weave, the theoretical study of such geometry is of wide application. Non of the previous studies have considered compressibility in thread cross section during flattening specially in an elliptical form.

In this work an assumption has been made to restrict threads compressibility by the constancy of the perimeter of the elliptical cross section as a result of the mutual normal forces between warp and weft threads. In actual practice the perimeter also may be extended due to fibre elasticity.

The present theoretical analysis of the assumed elliptical model was superseded by a study of square plain fabric geometry of circular cross section, for ensuring a correct mean of checking the results of the derived equations i.e. when $(e=1)$.

The results of this study could include the relations between cover, crimp, weight and fabric weave angle under different flattening values.

3. GEOMETRY OF SQUARE PLAIN FABRIC:

3.1 Circular Thread Cross Section:

Assumptions :

- Warp and weft thread diameters are equal;
- Warp and weft thread settings are equal;
- The bending resistance of the threads is negligible;
- No consideration of internal forces;
- The threads are inextensible;
- The threads are uncompressible;
- Interference between two succeeding threads is zero as shown in Fig. 1.

Fig. 1 shows a warp cross section of plain weave using the above assumptions. From this geometrical model the following properties such as K , C and W^* can be calculated as a function of weave angle ranging from $\theta = 0^\circ$ to $\theta = 60^\circ$ (jamming condition) as follows;

3.1.1 Relation between cover factor (K) and weave angle (θ):

The ratio of thread diameter to its spacing (d/p) expresses the relative closeness of threads, this ratio also expresses the fractional area of the cloth covered by the warp or weft threads. Therefore it can be called the fractional cover [5], and calculated as follows ;

From triangle (OAB) , Fig. (1)

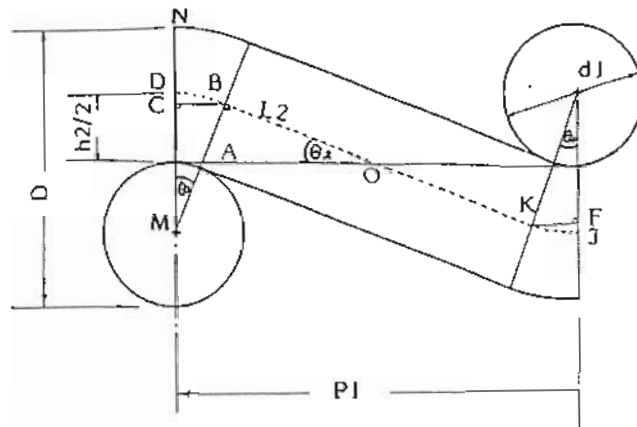


Fig. 1 : Geometry of circular thread cross section.

$$\sin \theta_2 = \frac{AB}{OA} = \frac{d_1 - \frac{d_1}{2} \sec \theta_2}{\frac{p_1}{2} - \frac{d_1}{2} \tan \theta_2} \quad \dots (1)$$

Hence $\frac{1}{2} \sin \theta_2 - \frac{d_1}{2p_1} \tan \theta_2 \sin \theta_2 = \frac{d_1}{p_1} - \frac{d_1}{2p_1} \sec \theta_2$

Now Equation (1) becomes

$$\frac{1}{2} \sin \theta_2 \cos \theta_2 + \frac{d_1}{2p_1} \cos^2 \theta_2 = \frac{c_1}{p_1} \cos \theta_2$$

Then $\frac{d_1}{p_1} = \sin \theta_2 / (2 - \cos \theta_2)$... (2)

and warp cover factor $K_1 = 28 \sin \theta_2 / (2 - \cos \theta_2)$... (3)
and similar (K_2) can be obtained.

Hence fabric cover factor (K_c) can be calculated from the following equation.

$$K_c = K \left(2 - \frac{K}{28} \right) \quad \dots (4)$$

3.1.2 Relation between crimp percentage (C) and weave angle (θ):

The equation for the crimp percentage can be written as follows;

$$C_2 = \left(\frac{L_2}{p_1} - 1 \right) \times 100, \quad (\%)$$

From Fig. 1, L_2 is given as follows

$$L_2 = \text{straight line (BK)} + \text{two arcs DB and JK}$$

$$= 2 \text{ OB} + 2 \widehat{\text{BD}}$$

$$= 2 \left[\left(\frac{p_1}{2} - d_1 \sin \theta_2 \right) \sec \theta_2 + \frac{\pi}{180} d_1 \theta_2 \right]$$

Then $C_2 = \left[\left(\sec \theta_2 - \frac{2d_1}{p_1} \tan \theta_2 + \frac{2\pi}{180} \cdot \frac{d_1}{p_1} \cdot \theta_2 \right) - 1 \right] \times 100$... (5)

Substituting Equation (2) into Equation (5) will give the thread crimp percentage for a given weave angle

$$\text{thus } C_2 = \left[\frac{\sin \theta_2}{2 - \cos \theta_2} \left(\frac{2\pi}{180} \cdot \theta_2 - 2 \tan \theta_2 \right) + \sec \theta_2 - 1 \right] \times 100 \quad \dots (6)$$

1.3 Relation between relative Fabric weight (W^*), and weave angle (θ):

Fabric weight per unit area can be determined as follows;

$$W = 2 \left[0.1n \cdot T \left(1 + \frac{C}{100} \right) \right], \quad (\text{g/M}^2)$$

$$\begin{aligned} W^* &= \frac{W}{W_{\max}} = \frac{n}{n_{\max}} \cdot \frac{(100 + C)}{(100 + C_{\max})} \\ &= \frac{P_{\min}}{p} \cdot \frac{(100 + C)}{(100 + C_{\max})} \quad \dots (7) \\ &= \frac{d}{p} \cdot \frac{P_{\min}}{d} \cdot \frac{(100 + C)}{(100 + C_{\max})} \end{aligned}$$

From Table (1)

$$= \frac{\sin \theta_2}{2 - \cos \theta_2} \cdot \frac{1}{0.5774} \cdot \frac{(100 + C)}{(100 + 20.9135)} = 0.01484 \frac{\sin \theta_2}{2 - \cos \theta_2} (100 + C) \quad \dots (8)$$

Values of K , K_c and C against weave angle (θ) could be calculated from Equations 3, 4 and 6 respectively and tabulated in Table 1. Fig. 2 shows these values represented as a relative percent of their maximum values at ($\theta = 60^\circ$) beside relative fabric weight (W^*) which is calculated from Equation (8).

Table 1: Values of $\frac{d}{p}$, K , K_c and C at different values of (θ)

θ°	d/p	K	K_c	C
0	0	0	0	0
5	0.0868	2.431	4.651	0.3757
10	0.1710	4.789	8.759	1.4774
15	0.2503	7.008	12.262	3.2221
20	0.3226	9.032	15.151	5.4587
25	0.3864	10.820	17.459	8.0255
30	0.4409	12.346	19.248	10.7303
	0.4857	13.601	20.595	13.3988
	0.5209	14.586	21.574	15.8558
45	0.5469	15.314	22.252	17.9471
50	0.5644	15.804	22.688	19.5500
55	0.5743	16.808	22.925	20.5603
60	0.5774	16.166	22.998	20.9135

3.2 Elliptical Thread Cross section:

Assumptions :

- Warp and weft thread diameters are equal;
- Warp and weft thread settings are equal;
- The bending resistance of the threads is negligible;
- The threads are inextensible;

interference between two succeeding threads is zero as shown in Fig.3.

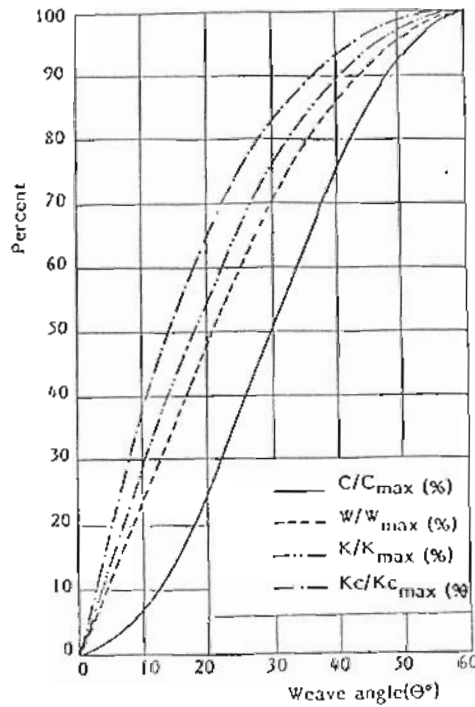


Fig. 2: Relation between relative percent of crimp, thread cover, fabric cover, weight and weave angle (θ).

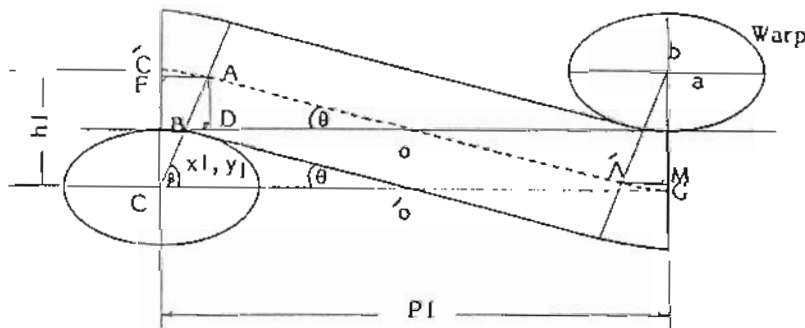


Fig. 3: Geometry of elliptical thread cross section.

Assuming a woven thread with a circular cross section was flattened under the effect of either internally or externally flattening force to an elliptical shape. Two separate possibilities could be imagined to define such behaviour either constancy of area or perimeter of thread cross section.

The first assumption means that the threads are incompressible more over it implies that the thread perimeter will inevitably increase (i.e. $P_e/P_c \geq 1$) as shown from the following equations:

If there is no change in area

$$\therefore \pi r^2 = \pi ab$$

which means that $e = b/a = r^2/a^2$... (9)

∴ Elliptical perimeter with respect to the circular perimeter (P_e/P_c) =

$$= 2\pi \sqrt{1/2(a^2 + b^2)} / 2\pi r$$

$$P_e/P_c = [1/2 \left(\frac{a^2 + b^2}{r^2} \right)]^{1/2} \geq 1$$

as it easy to prove that $\frac{a^2 + b^2}{r^2} \geq 2$

The second possibility means that the area of cross section will inevitably decrease allowing compressibility to take place-which is nearer to reality- i.e. ($A_e/A_c \leq 1$) as shown from

Table II which is based on the following equation :

At constancy thread perimeter

$$\therefore 2\pi r = 2\pi \sqrt{1/2(a^2 + b^2)}$$

$$\therefore b/r = \sqrt{2 - \left(\frac{a}{r}\right)^2} \dots (10)$$

Table II: Values of flattening factor (e) and (A_e/A_c) against (a/r)

a/r	b/r	e = b/a	$A_e/A_c = \pi ab / \pi r^2$
1	1	1	1
1.0250	0.9744	0.9506	0.9987
1.0500	0.9474	0.9023	0.9948
1.0750	0.9189	0.8548	0.9878
1.1000	0.8800	0.8080	0.9680
1.1250	0.8570	0.7617	0.9641
1.1500	0.8230	0.7157	0.9465
1.1750	0.7870	0.6698	0.9247

In reality either change in area and perimeter could occurred simultaneously but this is out of scope of this study.

3.2.1 Calculation of Maximum Weave Angle (θ) :

From Fig. 3

$$h_1 = (L_2 - 2 \widehat{AC}) \sin \theta + 2(2b - AC \sin \beta) \dots (11)$$

$$\text{where } AC = \sqrt{[(a + b) \cos \beta]^2 + (2b \sin \beta)^2} \dots (12)$$

$$\text{In the case of jamming, } L_2 - 2 \widehat{AC} = 0 \dots (13)$$

Substituting Eq. (12) and Eq. (13) into Eq. (11)

$$\therefore h_1 = 4b - 2b \sin \beta \sqrt{\frac{(1 + e)^2}{e^2} \cos^2 \beta + 4 \sin^2 \beta}$$

$$\therefore D = 2 h_1 = 4b$$

$$\therefore h_1 = D \left(1 - 1/2 \sin \beta \sqrt{\frac{(1 + e)^2}{e^2} \cos^2 \beta + 4 \sin^2 \beta} \right)$$

$$\text{Hence } \frac{(1 + e)^2}{e^2} \cos^2 \beta + 4 \sin^2 \beta = 1/\sin^2 \beta \dots (14)$$

It is necessary to find the relationship between Θ and β as follows;
From Fig.3, the equation of straight line CB can be written as the following

$$y_1 = x_1 \tan \beta \quad \dots (15)$$

$$\text{and } \frac{x_1^2}{a^2} + \frac{x_1^2 \tan^2 \beta}{b^2} = 1$$

$$x_1 = [1 / (\frac{1}{a^2} + \frac{\tan^2 \beta}{b^2})]^{1/2} \quad \dots (16)$$

$$\therefore \tan \beta = y_1 / x_1$$

Substituting Eq. (16) into Eq. (15)

$$\therefore y_1 = \tan \beta [1 / (\frac{1}{a^2} + \frac{\tan^2 \beta}{b^2})]^{1/2}$$

$$\therefore \frac{x_1^2}{a^2} + \frac{y_1^2}{b^2} = 1 \quad \dots (17)$$

Differentiating Eq. (17) gives

$$\frac{d y_1}{d x_1} = -\frac{b^2}{a^2} \cdot \frac{x_1}{y_1} \quad \dots (18)$$

$$\text{also } \frac{d y_1}{d x_1} = \tan (\pi - \Theta) \quad \dots (19)$$

With equality of Eq. (18) and Eq. (19)

$$\therefore \tan \beta = e^2 / \tan \Theta \quad \dots (20)$$

Substituting Eq. (20) in Eq. (14) will give

$$\frac{(1+e)^2 \tan^2 \Theta}{e^2 (e^4 + \tan^2 \Theta)} + \frac{4e^4}{(e^4 + \tan^2 \Theta)} - \frac{e^4 + \tan^2 \Theta}{e^4} = 0 \quad \dots (21)$$

By solving Eq. (21) graphically, it was found that the maximum values of weave angle (Θ) corresponded to the different values of flattening factor (e) are $\Theta = 60^\circ$ (at $e=1$), 58° (at $e = 0.9506$), 56° (at $e = 0.9023$), 54° (at $e = 0.8548$), 52° (at $e = 0.808$) and 49.5° (at $e = 0.7617$) respectively.

3.2.2 Relation Between Cover Factor (K) and Weave Angle (Θ) at Different Values of Flattening Factor (e):

From Fig. 3

$$\tan \Theta = \frac{AD}{CD} = \frac{2b \sin \beta - b}{\frac{p}{2} - (a+b) \cos \beta}$$

$$\text{i.e. } \tan \Theta = \frac{\frac{2ea}{p} \sin \beta - \frac{ea}{p}}{\frac{1}{2} - \frac{a(1+e)}{p}} \cdot \cos \beta$$

$$\text{Thus } \frac{1}{2} \tan \Theta - \frac{a(1+e)}{p} \cos \beta \cdot \tan \Theta = \frac{2ea}{p} \sin \beta - \frac{ea}{p}$$

$$\therefore \tan \Theta = \frac{2a}{p} [(1 + e) \cos \beta \cdot \tan \Theta + 2e \sin \beta - e]$$

$$\therefore \frac{2a}{p} = \frac{\tan \Theta}{(1 + e) \cos \beta \cdot \tan \Theta + 2e \sin \beta - e} \dots (22)$$

Substituting Eq. (20) in Eq. (22)

$$\therefore \frac{2a}{p} = \frac{\tan \Theta}{\frac{(1 + e) \tan^2 \Theta}{\sqrt{e^4 + \tan^2 \Theta}} + \frac{2e^3}{\sqrt{e^4 + \tan^2 \Theta}} - e} \dots (23)$$

Therefore, thread cover factor (K) =

$$= \frac{28 \tan \Theta \cdot \sqrt{e^4 + \tan^2 \Theta}}{(1 + e) \cdot \tan^2 \Theta + 2e^3 - e \sqrt{e^4 + \tan^2 \Theta}} \dots (24)$$

The results of thread and fabric cover factor against weave angle (Θ) at various flattening factors are shown in Fig.4.

3.2.3 Relation Between Crimp Percentage (C) and Weave Angle (Θ) for Different Values of Flattening factor (e):

3.2.3.1 Calculation of the ratio of straight thread length to the thread spacing (2OA/P):

From Fig. 3

$$h_1 = 2b = 2OA \sin \Theta + 2(2b - AC \sin \beta)$$

$$\text{or } OA = \frac{1}{\sin \Theta} (AC \sin \beta - b) \dots (25)$$

$$\text{where } AC = \sqrt{[(a + b) \cos \beta]^2 + (2b \sin \beta)^2} \dots (26)$$

Substituting Eq. (26) into Eq. (25)

$$\therefore \frac{2 \cdot OA}{p} = \left[\frac{2 \sin \beta}{p \sin \Theta} \sqrt{[(a + b) \cos \beta]^2 + (2b \sin \beta)^2} - \frac{2b}{p \sin \Theta} \right] \dots (27)$$


Now Equation (27) becomes

$$\frac{2 \cdot OA}{p} = \left(\frac{2a}{p} \right) \cdot \frac{1}{\sin \Theta} \left[\sin \beta \sqrt{(1 + e)^2 \cos^2 \beta + 4e^2 \sin^2 \beta} - e \right] \dots (28)$$

3.2.3.2 Calculation of the ratio of curved thread length to thread spacing (2A'C/P):

From Fig. 3, the perimeter (P_e) of the shown ellipse can be calculated [6] approximately as the following equation.

$$P_e = 4(a + b) \int_{\beta=0}^{\beta=\pi/2} \sqrt{1 - k^2 \sin^2 \beta} \cdot d\beta$$

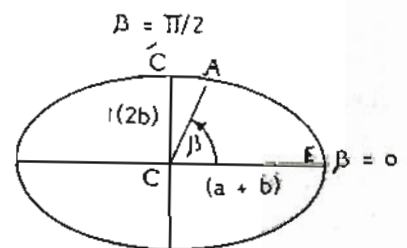

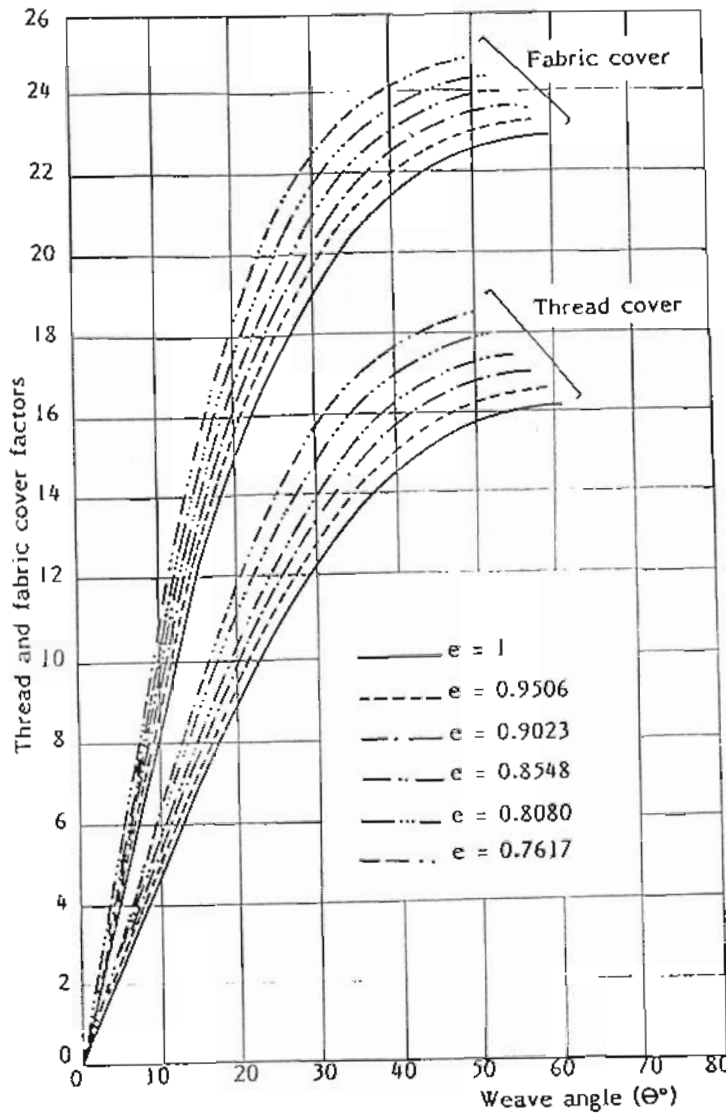


Fig. 4: Relation between thread cover factor, fabric cover factor and weave angle (θ) at different values of flattening factor (e).

where $K = \sqrt{(a + b)^2 - (2b)^2} / (a + b)$

i.e. $K^2 = [1 - \frac{4e^2}{(1 + e)^2}]$

Therefore $\frac{p}{4}e = a(1 + e) \int_{\beta = 0}^{\beta = \pi/2} \sqrt{1 - \sin^2 \beta [1 - \frac{4e^2}{(1 + e)^2}]} \cdot d\beta$

$$\text{Then arc length } AE \text{ (at angle } \beta) = a(1+e) \int_0^{\beta} \sqrt{1 - \sin^2 \beta \left[1 - \frac{4e^2}{(1+e)^2}\right]} d\beta \quad \dots (29)$$

By using the numerical integration method of Eq. (29), arc length AE could be calculated at different values of β -correspondent to weave angle (Θ) From Eq. 21-until $\beta = 90^\circ$. Therefore

$$\frac{2AC}{p} = \frac{2a}{p} (1+e) \left[\int_0^{\pi/2} \sqrt{1 - \sin^2 \beta \left[1 - \frac{4e^2}{(1+e)^2}\right]} d\beta - \int_0^{\beta} \sqrt{1 - \sin^2 \beta \left[1 - \frac{4e^2}{(1+e)^2}\right]} d\beta \right] \quad \dots (30)$$

Equations (28) and (30) which are both illustrated in Fig. 5 shows clearly that the increase of weave angle (Θ) increase the thread length which wraps over the crossing thread while decrease the straight line portion which joint the two curve parts. Fig. 6 shows the crimp percentage (C) against (Θ) using the simple crimp equation

$$C = \left[\left(\frac{20A}{p} + \frac{2AC}{p} \right) - 1 \right] \times 100 \quad \dots (31)$$

The crimp percentage (C) could also be illustrated against (β) using the previous derived relation between (Θ, β), where both the increase of weave angle (Θ) and the decrease of angle (β) have a similar effect on increasing the crimp (C), while the effect of flattening factor (e) is contradicting as shown in Figures 6 and 7.

3.2.4 Relation Between Thread Cover Factor (K) and Correspondent Crimp (C) at Different Values of (e):

From Fig. 4 and Fig. 6 the thread crimp (C) could be plotted against thread cover factor (K) as shown in Fig. 8 at different values of (e) which could be of practical importance i.e. predicting any of the three mentioned parameters (K, C, e) by knowing the other two. Also both thread length (L) and its correspondent spacing (p) related to the semi-major axis of the elliptical thread cross section (a) are plotted against each other in Fig. 9 which shows almost straight line ($r = 0.999$) irrespective of flattening factor (e), this means that (L) increases by the increase of thread spacing (P) irrespective of what so ever the value of flattening factor (e).

3.2.5 Relation Between Relative Weight (W^*) and Weave Angle (Θ) at Different Values of Flattening Factor (e):

Equation (7) can be rewritten as follows;

$$W^* = \left(\frac{2a}{p} \right) \cdot \left(\frac{P_{\min}}{2a} \right) \cdot \left(\frac{100 + C}{100 + C_{\max}} \right) \quad \dots (32)$$

By substituting in Eq. (32) from Eq. (23) will give

$$W^* = \frac{\tan \Theta}{\left[\frac{(1+e) \tan^2 \Theta}{\sqrt{e^4 + \tan^2 \Theta}} + \frac{2e^3}{\sqrt{e^4 + \tan^2 \Theta}} - e \right]} \cdot \left(\frac{P_{\min}}{2a} \right) \cdot \left(\frac{100 + C}{100 + C_{\max}} \right) \quad \dots (33)$$

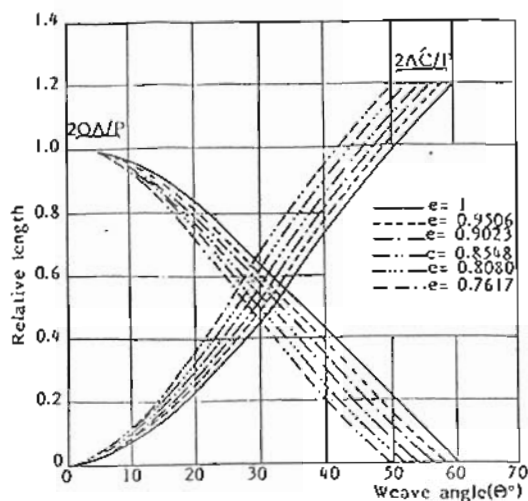


Fig.5: Relation between straight line length of thread axis relative to thread spacing ($2OA/P$), wrapped arc length of thread axis relative to thread spacing ($2AC/P$) and weave angle (θ) at different values of flattening factor (e).

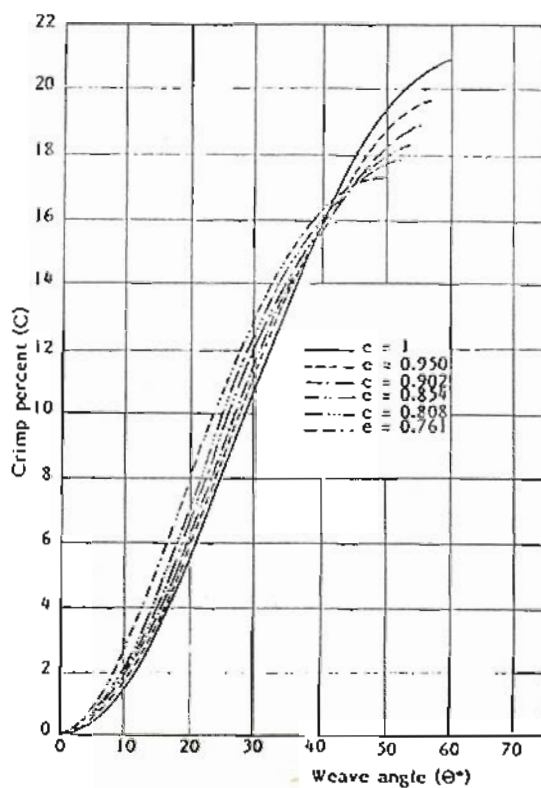


Fig. 6: Relation between crimp percent (C) and weave angle (θ) at different values of flattening factor (e)

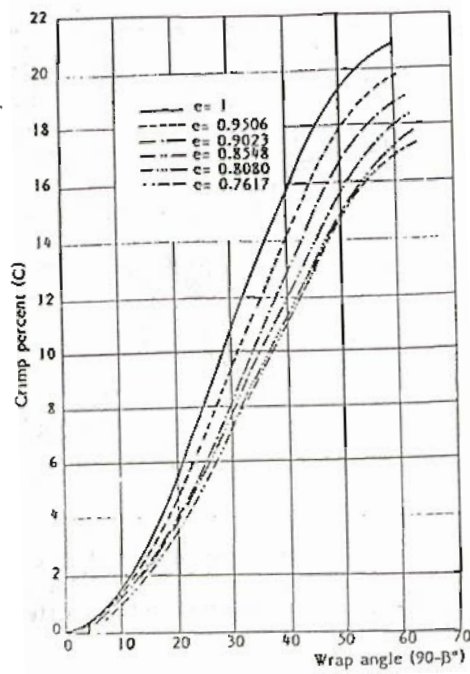


Fig. 7: Relation between crimp percent (C) and wrap angle ($90-\beta^\circ$) at different values of flattening factor (e)

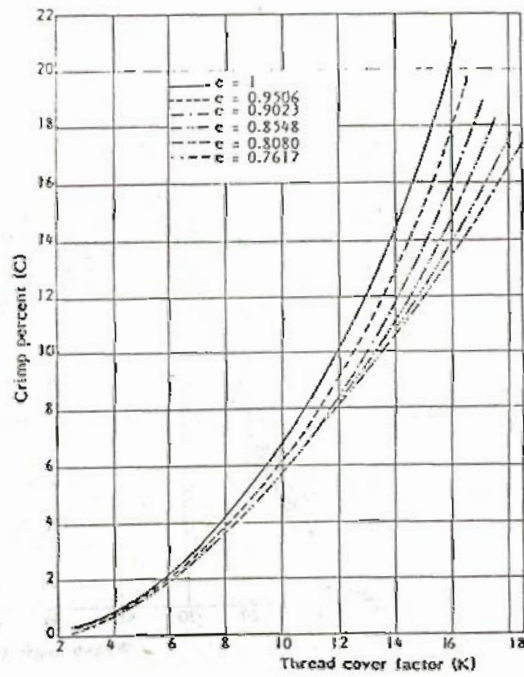


Fig. 8: Crimp percent (C) plotted versus thread cover factor (K) at different values of flattening factor (e).

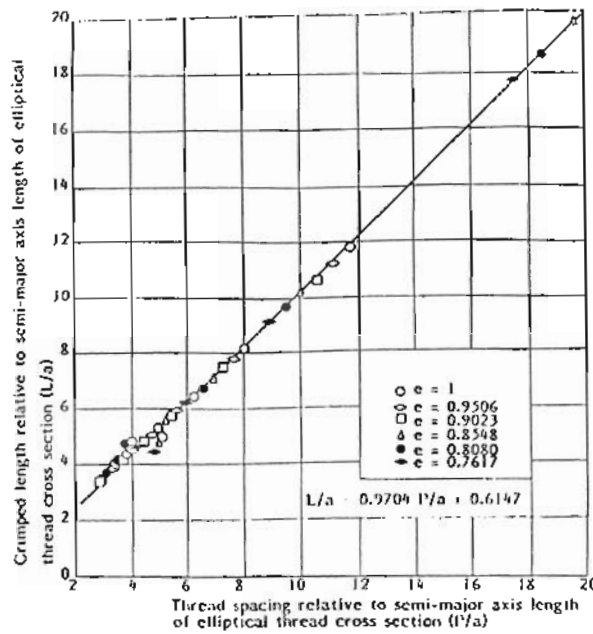


Fig. 9: Crimped length relative to semi-major axis length of elliptical thread cross Section (L/a) plotted against thread spacing relative to semi-major axis length of elliptical thread cross section (P/a) for different values of flattening factor (e)

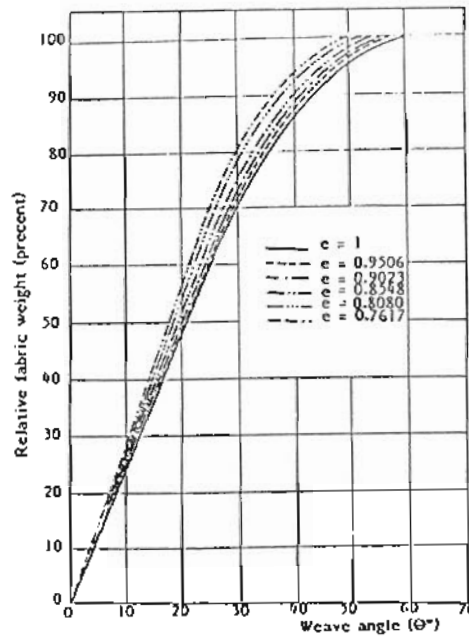


Fig. 10: Relation between relative fabric weight (W^*) and weave angle (Θ) at different values of flattening factor (e)

The values of $P_{\min}/2a$, C_{\max} (at jamming conditions) could be obtained from Equations (23), (31) at different values of flattening factor (e).

Values of W^* could be plotted against weave angle (Θ) at different values of (e) as shown in Fig. 10.

4. DISCUSSION AND CONCLUSION

- The decrease in maximum weave angle (Θ_{\max}) with more thread flattening-which is expected-means that with threads of high ability to be flattened e.g. low twisted continuous filament yarn will reach maximum thread setting at lower density than those of highly twisted spun yarns.
- Both thread cover factor (K) and consequently fabric cover factor (Kc) increase by flattening degree ($1/e$) depending on weave angle (Θ), this is considered as an advantage to gain more cover with the same thread density or the same cover with less thread density.
- The weave angle (Θ) decreases with degree of flattening ($1/e$) depending on the value of thread cover (K). Such decrease in (Θ) may result in decreasing the normal mutual forces between warp and weft and hence the frictional forces which keeps the firms. This is not considered as an advantage.
- The wrap angle ($90 - \beta^\circ$) increases with flattening degree ($1/e$) which may improve yarn to yarn friction through the increase of contact area. This effect seems to be contradicted to the previous one.
- The crimp % (C) increased very slightly with the increase of flattening degree ($1/e$) up to weave angle 45° then begins to decrease until reaching their maximum weave angle (Θ_{\max}).
- The flattening factor seems to have no effect on thread length (L) that is to say when the fabric is exposed to external flattening forces the thread length stay constant under any pressure and hence fabric dimensions. This is due to the approximate equivalent increase and decrease of arc length and straight length of thread respectively. This makes a distinction between fabric and other solid matter which increase in dimensions with increasing of flattening degree such behaviour is considered to be a great advantage.
- The relative weight (W^*) seem to increase linearly with weave angle (Θ)-up to 40° approximately - with very less effect with flattening factor (e). Fabric weight-in this case-as a function of cover and crimp may be the reason, it may be also important to remember that constant (Θ) does not mean constant thread spacing (P) as it is function in both thread spacing (P) and thread minor axis ($2b$) of the elliptical cross section which is in turn function in flattening factor (e).

REFERENCES

- 1- I. P.T. Peirce The geometry of cloth structure J.T.I., Vol. 28, T. 45, 1937.
- 2- E.V. Painter, Text. Res. J., Vol. 22, P. 153, 1952 .
- 3- A.J. Kemp, The extension of peirce's cloth geometry to the treatment of non-circular threads . J. Text. Inst., Vol. 49, T. 44, 1958.
4. Г. Б. Ааманов, У. З. Бачев и Н. Ф. Сурнина, Строение Ткани и Современние Методы Проектирования, Москва, 1984.
5. A. T. C. Robinson and R. Marks, Woven Cloth Construction, Chapter 1, Manchester, 1973.
6. M. R. Spiegel, Mathematical Handbook of Formulas and Tables, Schaum's outline series, p. 7, 1968.