

5-23-2021

## An Investigation to the Influence of Sizing Machine Settings on Thread Properties.

M. Salama

*Textile Engineering Department., Faculty of Engineering., El-Mansoura University., Mansoura., Egypt.*

M. El-Missery

*Textile Engineering Department., Faculty of Engineering., Alexandria University., Alexandria., Egypt.*

S. Ibrahim

*Textile Engineering Department., Faculty of Engineering., El-Mansoura University., Mansoura., Egypt.*

H. Behes

*Textile Engineering Department., Faculty of Engineering., El-Mansoura University., Mansoura., Egypt.*

Follow this and additional works at: <https://mej.researchcommons.org/home>

---

### Recommended Citation

Salama, M.; El-Missery, M.; Ibrahim, S.; and Behes, H. (2021) "An Investigation to the Influence of Sizing Machine Settings on Thread Properties.," *Mansoura Engineering Journal*: Vol. 15 : Iss. 2 , Article 33. Available at: <https://doi.org/10.21608/bfemu.2021.171559>

This Original Study is brought to you for free and open access by Mansoura Engineering Journal. It has been accepted for inclusion in Mansoura Engineering Journal by an authorized editor of Mansoura Engineering Journal. For more information, please contact [mej@mans.edu.eg](mailto:mej@mans.edu.eg).

AN INVESTIGATION TO THE INFLUENCE OF SIZING  
MACHINE SETTINGS ON THREAD PROPERTIES

by

\* \* \* \* \*  
M. Salama , M. El-Missery , S. Ibrahim and H. Behes  
-----

بحث تأثير ضبطات ماكينة البوش على خواص الخيوط

الخلاصة:

فرض هذا البحث هو محاولة بحث تأثير الضبطات المختلفة لماكينة البوش على الخواص الميكانيكية والاحتكاكية للخيوط المبوثة وكذلك نسبة البوش المكتسبة. بينت النتائج وجود ارتباط كبير بين قوة الشد في المناطق المختلفة ودرجة حرارة التجفيف وضغط المعاصرات وخواص الخيوط المبوثة بما يتطلب إعادة التقييم للضبطات المستخدمة للحصول على أفضل النتائج.

ABSTRACT:

-----  
The objective of the present work is to investigate the influence of the sizing machine settings on the tensile and frictional properties of the sized yarn as well as the %size add-on. A significant effect on the properties of the sized yarns was found due to the tension in the different zones, drying temperature and squeezing pressure.

1. INTRODUCTION:

-----  
The warp threads are subjected to a high-repeated abrasion and tensile stresses during weaving. This may cause a warp break, the matter which reduces both, loom productivity and fabric quality. For high speed weaving it becomes necessary to have a well prepared warp threads to withstand high stresses during weaving. This is also important to improve the economics of the weaving process, because cost of the weaving machine is high (about 250,000 L.E. for a Sulzer weaving machine).

Generally, the quality of yarn from spinning has a large influence on the performance of warp threads during weaving. However, the yarn preparation for weaving, specially the sizing process, determines to a large extent the properties of warp threads which are required to produce a high quality fabrics on a high speed loom. It has been reported [5] that, for a high production loom, the warp threads should fulfil the following requirements:

- 1-Sufficient resistance to abrasion and adequate thread strength.
- 2-High and even residual stretch and even tension.
- 3-Slight hairiness and curliness.
- 4-No crossings in the thread run.

The yarn, after sizing, should have more than 70% of its original stretch. It has been shown [3] that, the increase in the sizing stretch causes an increase in the warp end breakage rate during weaving. The increase in size encapsulation and size penetration up to 30% results in a reduction in the relative warp end breakage during weaving. A high size penetration will have a bad effect on end breakage rate.

\*Mansoura University  
\*\*Alexandria University



Figure(2) shows the principle of friction measurement. The measurement of friction was carried out at speeds of 20 mt/m. & 30 mt/m. which simulate the running speed of a warp on a modern weaving machine.

The abrasion resistance of the sized yarns was found in terms of the number of cycles to breakage at speed of 1000 cycl/m. The Meyefem Type FY-10 tester was used and Figure(3) shows the principle of measurement.

The %size add on was found by weighing a 10 mt. of yarn before and after sizing.

### 3-RESULTS AND DISCUSSIONS:

In order to investigate the variation in the thread properties along the warp width, which might happen from the squeezing rollers. The warp width was divided into seven equal sections, each was 20 cm. The tensile properties of threads in each section was found at different squeezing pressures. Table(1) shows the results of the variance analysis of thread properties along warp width. It is clear that the variation in thread properties along warp width is not significant at confidence limits of 95% & 99%.

The results of the experimental work are shown in Figures(4 to 13) and Tables(2&3). Table(4) shows the correlation coefficient of sizing machine settings and some of thread properties. The significant effects are considered.

#### 3.1. Effect of let-off tension on thread properties.

##### 3.1.1. Tensile properties of threads.

Figure(4) shows the influence of let-off tension on the tensile properties of the threads. The experimental results showed that the increase in warp let-off tension resulted in an increase in thread breaking strength, breaking extension, work of rupture and ballistic strength. This was observed up to a value of 500 N. let-off tension. Applying tension in this zone more than 500 N., reduced the tensile properties. Also, the increase in let-off tension resulted in a better equalisation to the tension differences between the threads which resulting from the previous processes. This is shown in Figure(4), the c.v.% of tensile properties decreased as the let-off tension was increased up to 550 N.

##### 3.1.2. Frictional properties of threads.

Figure(5) shows the effect of let-off tension on frictional properties of threads in terms of the coefficient of friction between thread and ceramic guide and the output tension of thread to thread friction. The results showed no clear trend to the effect of let-off tension on frictional properties of sized yarns.

#### 3.2. Effect of inlet tension on thread properties:

##### 3.2.1. Tensile properties of threads.

The breaking strength of the threads and its work of rupture decreased as the inlet tension was increased, as shown in Figure(6). This is because the threads in the size box were highly tensed. The matter which resulted in less size pick up than the case of the threads which immersed in the size box at relaxed state. Consequently, the breaking extension increased, as shown in Figure(6-c). At the same time the c.v.% of the thread strength, extension and work of rupture reduced as the

inlet tension was increased. This is attributed to the differences in yarn tension which resulted from the previous processes.

### 3.2.2. Frictional properties of threads.

Figure(7) shows that the coefficient of friction between the thread and ceramic guide and the output tension of thread to thread friction increased as the inlet tension was increased. This is attributed to the poor encapsulation of sized yarn which resulted from the small amount of size pick up with the increase in inlet tension. Hence, the abrasion resistance of sized yarn reduced, as shown in Table(2).

The experimental results of %size add on was not correlated to inlet tension. This is attributed to the experimental method to find the %size add-on and the variation in the amount of size pick up in the size box.

### 3.3. Effect of wet tension on thread properties:

#### 3.1. Tensile properties.

Generally, the tensile properties the sized yarn were influenced to a large extent by the wet tension, as shown in Figure(8). This is because, the warp threads in the wet state, after leaving the size box, stretch fast when tension was applied. It was reported that 2/3 of the stretching during sizing processes occurs in the wet region. This resulted in an increase in the breaking strength and a reduction in breaking extension of the sized yarn when the wet tension was increased. Hence, the work of rupture as well as the ballistic strength were influenced. In the present work, a wet tension higher than 400 N. showed a bad influence on the tensile properties of sized yarns, as shown in Figure(8). This is attributed to the fiber slippage which occurred at high wet tension.

#### 3.3.2. Frictional properties of threads.

The results show no large influence of wet tension on the coefficient of friction between thread and ceramic guide. At the same time the variation in the output tension of thread to thread friction with the wet tension does not show a clear trend and it is not correlated to the results of abrasion resistance of the sized yarn.

### 3.4. Effect of dry tension on thread properties:

#### 3.4.1. Tensile properties of threads.

The results show that the tensile properties of sized yarns are not influenced by the dry tension in the range of this study. This is attributed to the fact that dry tension is applied to obtain a clean threads splitting in the dry zone without thread breakages.

#### 3.4.2. Frictional properties of threads.

The frictional properties of the threads were affected by the dry tension, as shown in Figure(9) and Table(2). The coefficient of friction between thread and ceramic guide as well as the output tension of thread to thread friction increased as the dry tension was increased. This is attributed to the splitting of the threads against the adhesive force of sizing material. Which resulted in a damage to the size film on the threads. This damage is expected to be large when the dry tension is high. The matter which reduced the abrasion resistance of the threads.

3.5. Effect of squeezing pressure on thread properties:  
-----

3.5.1. Tensile properties of threads

Figure(10) shows that the tensile properties of sized yarn are highly influenced by the squeezing pressure. In spite of the reduction in the % size add-on, the breaking strength of threads increased as the squeezing pressure was raised up to 11.25 KN. This is attributed to the enhancement in size penetration. Hence, the thread elasticity was influenced. The matter which caused a reduction in the ballistic strength of the threads, as shown in Figure(10-d). A reduction in the c.v.% of tensile properties was observed with the increase of the squeezing pressure, as shown in Figure(10).

3.5.2. Frictional properties of threads.

The coefficient of friction as well as the output tension reduced with the increase of squeezing pressure up to 11.25 KN., as shown in Figure(11). This resulted from the good encapsulation and the reduction of hairiness of the threads[2&6]. Hence, the abrasion resistance of threads was increased, as shown in Table(2).

3.6. Effect of drying temperature on thread properties:  
-----

3.6.1. Tensile properties of threads.

The results show that, lowering the teflon cylinders temperature or the steel cylinders temperature to 100 C, had no clear influence on the tensile properties of the threads.

3.6.2. Frictional properties of threads

The coefficient of friction between the thread and ceramic guide as well as the output tension of thread to thread friction increased as the teflon cylinders temperature was raised, as shown in Figure(12). This is because the outer surface of the threads dried rapidly when the temperature of teflon cylinders was high. Which caused a damage to the size film on the surface of sized yarn after completed drying and splitting was taken place. Consequently, the abrasion resistance was influenced, as shown in Table(3). The steel cylinders temperature showed no influence on the frictional properties of the threads, as shown in Figure(13). It is important to mention that, for a cotton yarn, the maximum drying temperature recommended by the machinery manufacturer is 150 C. It is also recommended that the teflon cylinders temperature should be higher than the steel cylinders temperature in order to avoid sticking of threads to the teflon cylinders.

4. CONCLUSIONS:  
-----

The previous experimental work was done to get the trend of variation in thread properties with the sizing machine settings. From the observations and discussions the following conclusions can be drawn:

1-The variation in the yarn tensile properties along warp width due to the squeezing roller was not significant.

2-The increase in let-off tension up to 500 N. (0.7 cN/tex) improved the tensile properties of sized yarns as well as its coefficient of variation.

3-The tensile properties and abrasion resistance of sized yarns decreased as the inlet tension was increased.

4-The increase in wet tension up to 400 N.(.56cN/tex), improved the tensile properties of sized yarns.

5-High dry tension caused a reduction to the abrasion resistance of sized yarns.

6-High squeezing pressure increased the strength and abrasion resistance of sized yarns but its elasticity was reduced.

7-Care must be taken when raising the temperature of teflon cylinders to avoid sticking of the threads to the cylinders. This would have a bad influence on the abrasion resistance of sized yarns.

It is important to mention that the interaction between machine settings is expected to have a large influence on the properties of sized yarns and machine performance. This will be studied in further work.

Acknowledgements:

-----  
Special thanks goes to Dr. Abdel-Asim Mohamed , president of El-Nasr Spinning, Weaving and Dyeing Co., Mehalla El-Kubra , for allowing us to produce the samples of sized yarns in his company. Also deep appreciation to the engineers of the weaving section for their cooperation in producing the samples on the sizing machine.

REFERENCES:

- 
- 1-Bouer, H., " How to optimise Warp Sizing.",  
Textile Asia , June, 1987.
  - 2-Miyamoto, K., "Sizing Techniques.", Text for cotton weaving  
engineering course.  
Nagoya International Training Center, JICA.
  - 3-Salsman, K., "Modern Yarn Evaluation for Shuttleless Looms.",  
Seydel Companies seminar at Textile Consolidation  
fund, Nov. 3, 1989.
  - 4-Trauter, J. and Bottle, H., "Technological Aspects of  
High-Pressure squeezing.", The world Conference on  
Warp Sizing. Clemson, S.C. May 24-28, 1982.
  - 5-The Sizing, Report by Sucker+Muller, Sizing machinery  
manufacturer.
  - 6-Zell , Sizing machinery manufacturer.

Table(1) Variance analysis of thread properties along warp width

Thread property	Squeezing pressure	D.F.	S.S.	M.S.	F
Breaking Load	7KN	6	53874.29	8979.05	1.3
Breaking Extension	7KN	6	2.41	0.4	0.82
Work of Rupture	7KN	6	242663.31	40443.89	1.37
Breaking Load	8KN	6	43334.29	7222.38	1.82
Breaking Extension	8KN	6	4.61	0.77	1.67
Work of Rupture	8KN	6	194913.3	32485.55	1.17
Breaking Load	9KN	6	25974.29	4329.05	0.93
Breaking Extension	9KN	6	2.65	0.44	1.0
Work of Rupture	9KN	6	164280.3	27380.05	1.12

Values of F correspond to N1=6 & N2=63 are:  
 2.25 at confidence limit 95% ,and  
 3.12 at confidence limit 99%

Table(2) Effect of tension and squeezing pressure on yarn properties

Machine setting Yarn properties	Let-off tension (N)					Inlet tension (N)				
	350	400	450	500	550	100	150	200	250	300
% Size add-on	7.5	7.1	13.3	19	17.3	7.8	13.1	11.7	10.4	12.6
Abrasion resistance, cycles	88	109	134	76	59	250	310	179	92	77

Machine setting Yarn properties	Wet tension (N)					Dry tension (N)					Squeezing pres.(KN)		
	350	400	450	500	300	400	500	600	700	8.25	9.25	11.25	
% Size add-on	13.2	19.2	10.4	14.7	8.5	22.7	17.4	11.7	18	17	15.8	16.2	
Abrasion resis. cycles	236	544	392	350	237	212	120	273	152	115	140	153	




Table(3) Effect of drying temperature on yarn properties

Cylinder temperature C	Teflon cylinder				Steel cylinder					
	100	105	110	120	130	140	100	110	120	140
Yarn properties										
% Size add-on	26.4	24.2	23.4	9.6	10.7	6.4	28.8	33.2	33.3	20.
Abrasion resistance, cycles	280	240	257	583	121	172	342	430	440	55

Table(4) The correlation coefficient of sizing machine settings and yarn properties


Yarn property	W.R. %	C.V. %	B.Str. %	C.V. %	S.Ex. %	C.V. %	Ballistic Strength	Coeff. of Friction	O/P Tension	%Size add-on	A.R cycl
Machine setting											
Lat-off Tension	.44	-.48	.39	-.14	.42	-.46	.50	-.52	.08	.88	-.38
Inlet Tension	-.06	-.96	-.63	-.79	.43	-.77	.22	.82	.35	.92	-.87
Wet Tension	.23	-.38	.52	-.51	.05	-.69	-.23	-1.0	.16	-.15	.19
Dry Tension	-.26	.68	-.68	-.35	.42	-.64	-.10	.78	.67	.23	-.28
Squeeze Pressur	.95	-.84	1.0	-.98	.25	.10	-.81	-1.0	-.98	-.50	.93
Teflon Temp.	-.16	-.70	-.31	-.22	-.10	.22	-.08	.95	.50	-.94	-.24
Steel Temp.	-.44	.11	-.87	-.19	.25	.61	-.56	-.97	-.71	-.68	-.75

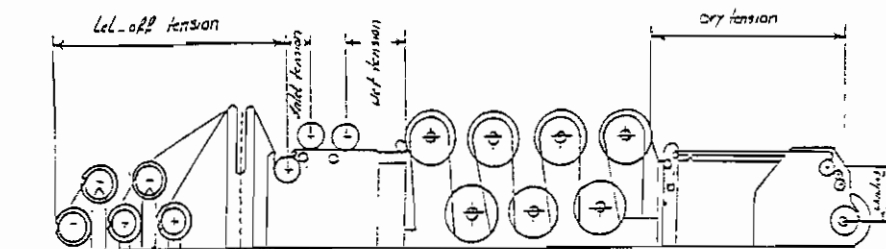


Figure(1) The sizing machine




Figure(2) Principle of friction measurement

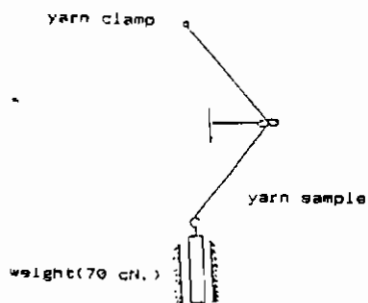


Figure(3) Principle of abrasion resistance measurement

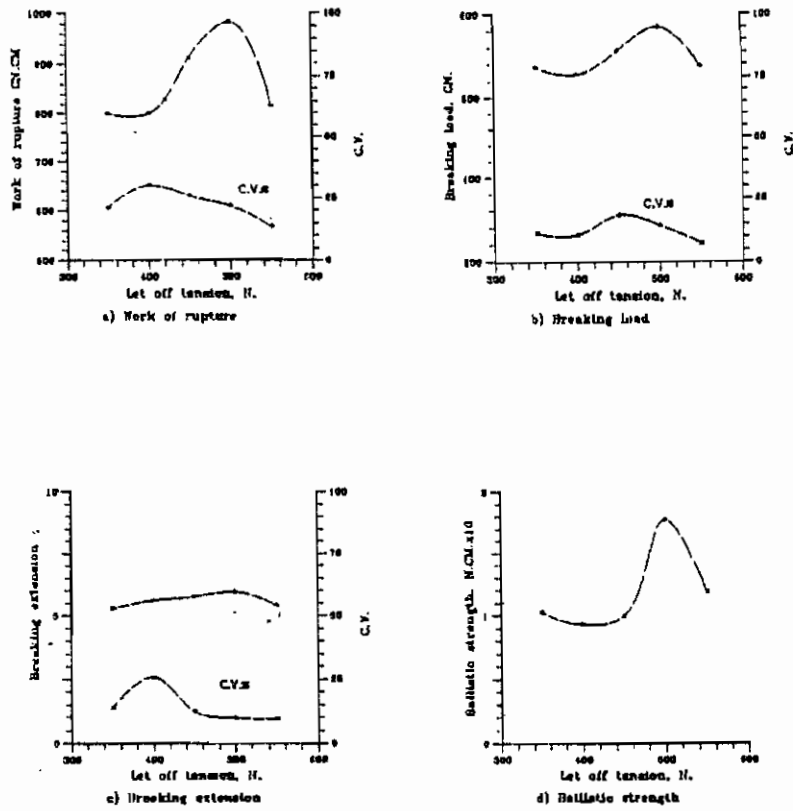


Figure(4) Effect of let-off tension on tensile properties of threads

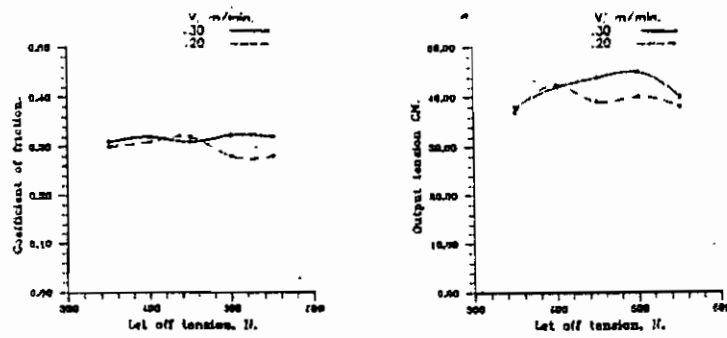


Figure(5) Effect of let-off tension on coefficient of friction and output tension

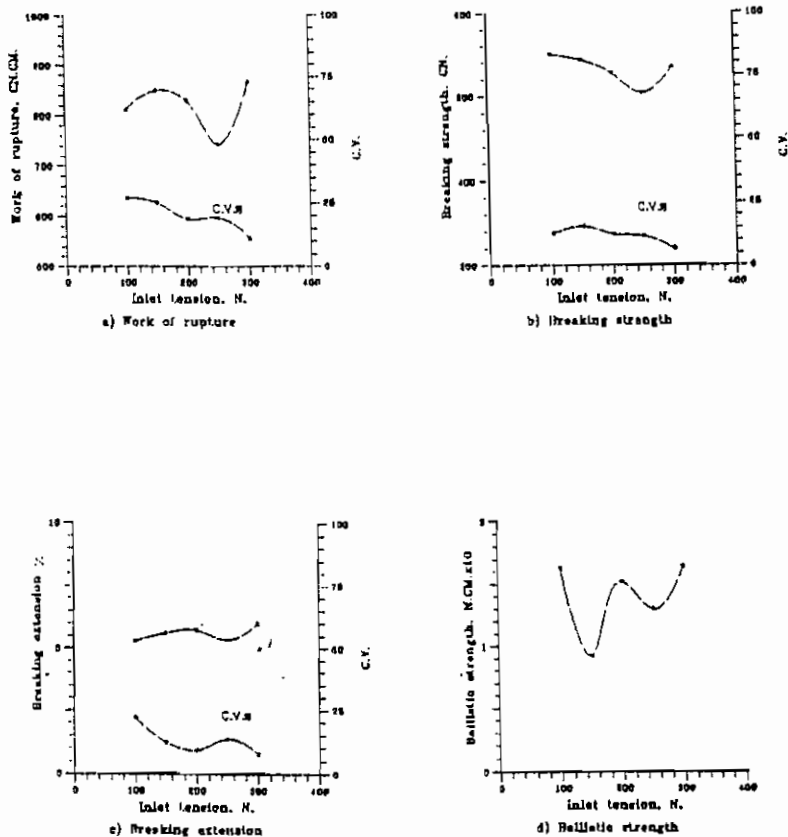


Figure(6) Effect of inlet tension on tensile properties of threads

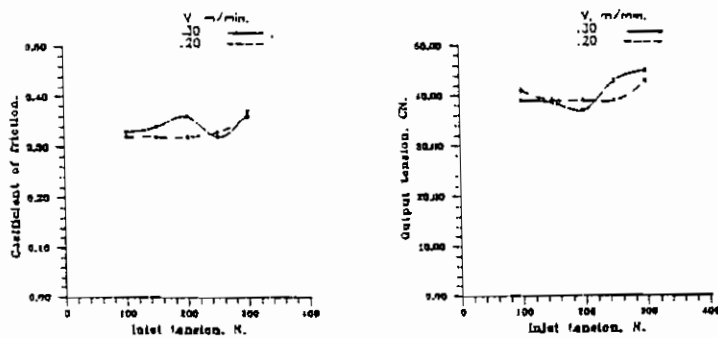


Figure(7) Effect of inlet tension on coefficient of friction and output tension

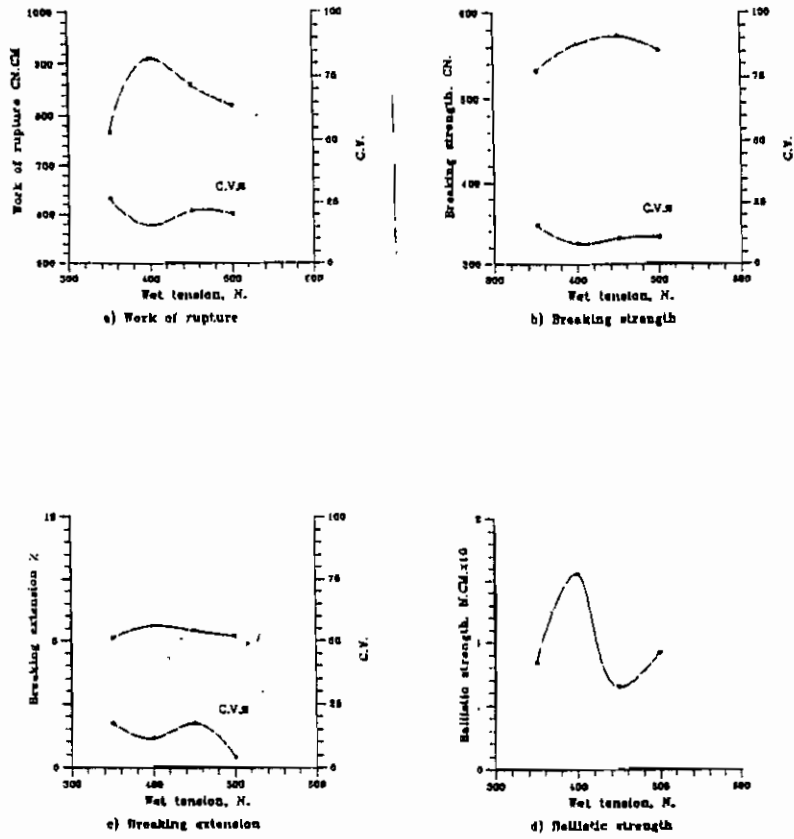


Figure(8) Effect of wet tension on tensile properties of threads

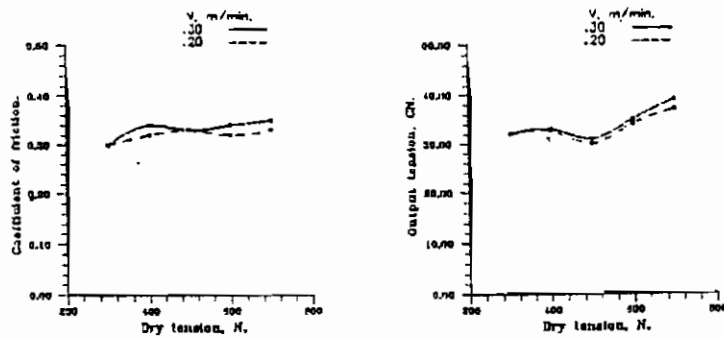


Figure(9) Effect of dry tension on coefficient of friction and output tension

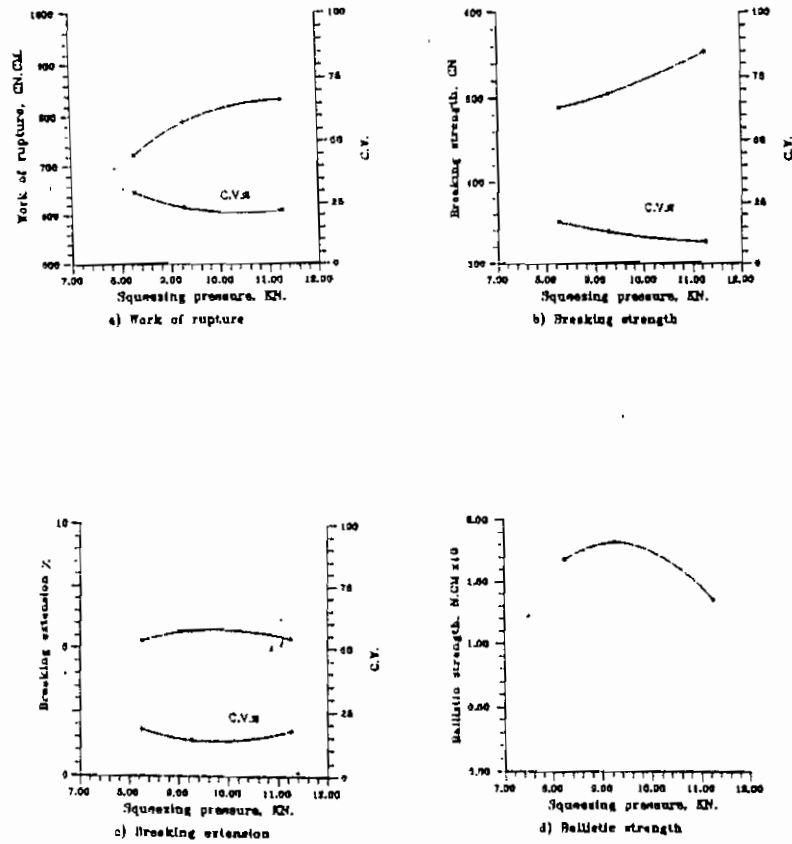


Figure(10) Effect of squeezing pressure on tensile properties of threads

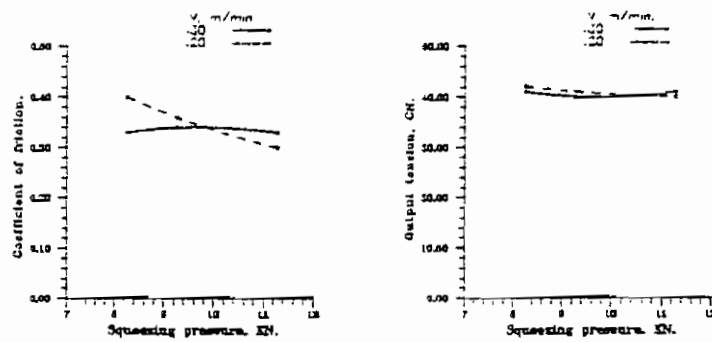

Figure(11) Effect of squeezing pressure on coefficient of friction and output tension

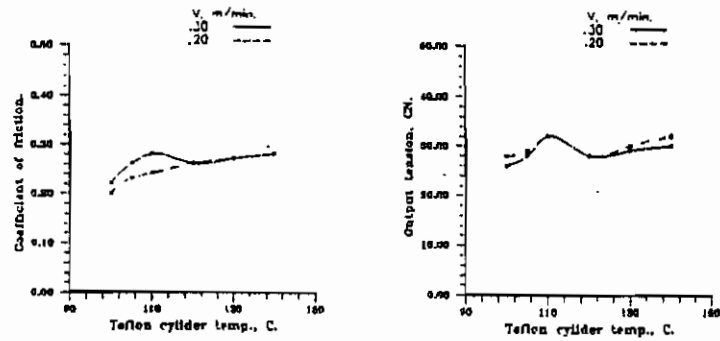

Figure(12) Effect of teflon cylinders temperature on coefficient of friction and output tension, steel cylinder temp. 130 C

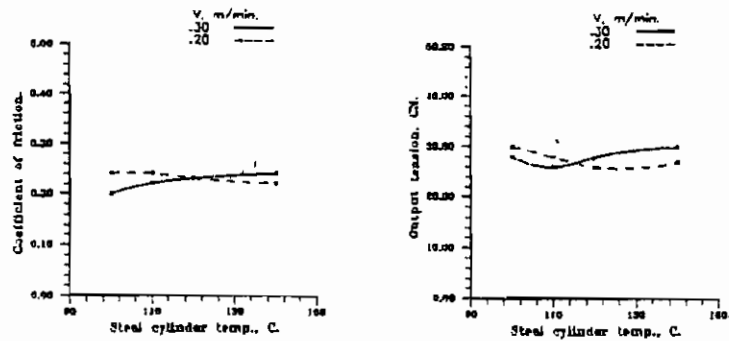

Figure(13) Effect of steel cylinders temperature on coefficient of friction and output tension, teflon cylinder temp. 130 C